

Materials Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: S. N. N. Bryntesen, I. Tolstorebrov, A. M. Svensson, P. Shearing, J. J. J. Lamb and O. S. Burheim, *Mater. Adv.*, 2022, DOI: 10.1039/D2MA00850E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Cite this: DOI: 00.0000/xxxxxxxxxx

Introducing Lignin as a Binder Material for the Aqueous Production of NMC111 Cathodes for Li-ion Batteries.[†]

Silje Nornes Bryntesen,^{*a} Ignat Tolstorebrov,^a Ann Mari Svensson,^b Paul Shearing,^{a,c} Jacob Joseph Lamb,^a and Odne Stokke Burheim^aReceived Date
Accepted Date

DOI: 00.0000/xxxxxxxxxx

By enabling water-based cathode processing, the energy-intensive *N*-methyl-2-pyrrolidone (NMP) recovery step can be eliminated, reducing the cost and environmental impact of LIBs. Aqueous processing of the high capacity Ni-containing $\text{LiNi}_x\text{Mn}_{1-x-y}\text{Co}_y\text{O}_2$ (NMC) cathodes is problematic due to lithium-ion (Li^+)-leaching, corrosion of the aluminum (Al) current collector, and the lack of aqueous soluble bio-derived binders. The present study investigates the potential of substituting and fully replacing the commonly used polyvinylidene fluoride (PVDF) and carboxymethyl cellulose (CMC) binders with abundant, bio-derived kraft lignin. The paper gives a holistic overview of the optimal conditions when employing these binders. For the first time, we demonstrate that NMC111 cathodes of comparable specific capacities to NMP/PVDF-based over 100 cycles or at high C-rates (5 C) can be formulated in water using lignin or CMC/lignin as binder materials. Cyclic voltammetry (CV) revealed that kraft lignin undergoes a redox reaction with the electrolyte between 2.8 - 4.5 V which diminishes upon subsequent cycles. Differential scanning calorimetry (DSC) revealed that lignin is thermally stable up to 152 °C. Rheology measurements showed that replacing NMP with water allows for a solvent reduction. The cathodes fabricated using an aqueous slurry should be dried at 50 °C, as extensive surface cracks detected using scanning electron microscopy (SEM) diminish. Li^+ -leaching from NMC111 and NaOH species from kraft lignin caused an increase in pH during the aqueous slurry fabrication. A carbon-coated Al-foil (C-Al) prevented Al corrosion and increased the lignin cathode's mechanical strength revealing lignin's exceptional binding abilities to carbon. The electrolyte wettability decreased for calendered lignin-containing cathodes with low porosity and a large carbon black/lignin matrix.

1 Introduction and Outline

Efforts to de-carbonize the transport sector are driving the shift from fossil-fuelled vehicles to electric mobility. Being the leading battery technology for mobile devices and battery electric vehicles (BEVs), recent advances in lithium-ion battery (LIB) technology has driven a rise in production

demand. However, the carbon footprint of LIB production contributes significantly to the greenhouse gas emissions of BEVs^{1,2}. Therefore, the sustainability and cost of production must be improved without compromising the battery energy density³.

LIB graphite anodes are usually fabricated using aqueous slurries, whereas cathodes are mainly produced using the toxic *N*-methyl-2-pyrrolidone (NMP) solvent. NMP introduces an expensive recovery step and requires high airflow during electrode drying⁴; thus, an aqueous cathode processing route will lower the energy consumption and cost of production⁵. Additionally, replacing the costly polyvinylidene fluoride (PVDF) cathode binder with water-soluble binders will simplify the recycling process for end-of-life LIBs by mitigating the conversion from solid-coated

^a Department of Energy and Process Engineering, Norwegian University of Science and Technology, Kolbjørn Hejes Vei 1B, N-7491 Trondheim, Norway. E-mail: odne.s.burheim@ntnu.no, silje.n.bryntesen@ntnu.no

^b Department of Materials Science and Engineering, Norwegian University of Science and Technology, Sem Sælands vei 12, N-7491 Trondheim, Norway.

^c University College London, Gower St, London, England.

[†] Electronic Supplementary Materials (ESI) available: In an separate file. See DOI: 00.0000/00000000.



cathodes to aqueous black mass⁶.

However, several challenges have been reported when transitioning to the aqueous processing of Ni-containing cathodes. Issues are related to the poor water-compatibility with the active material, high basicity of water leading to corrosion of the aluminum(Al)-foil current collector^{7,8}, cracking of the cathode coating due to increased capillary pressure during electrode drying⁹, and finding a binder material providing sufficient cohesion and adhesion forces between the coated particles and the Al-foil¹⁰, respectively. Therefore, the search for aqueous compatible and electrochemically inactive binders providing sufficient mechanical strength has become an area of significant scientific interest^{4,10–14}.

1.1 Aqueous Binder Materials

Bresser *et al.*¹³ reviewed alternative bio-derived aqueous binders for LIB electrodes. A typical example of a water-soluble and/or dispersible carboxymethyl cellulose/styrene-butadiene rubber (CMC/SBR) binder currently used in the production of the graphite anodes and water-compatible olivine structured LiFePO₄ (LFP) cathodes¹³. CMC is a linear polymeric derivative of cellulose and has been widely used as a thickener, binder, and stabilizer in various industries¹⁵. Furthermore, CMC has contributed to making the slurry homogeneous as it suppresses the re-agglomeration of the dispersed CB particles¹⁶. Understanding the interaction between the binder and the other electrode components (i.e., the active material and the conductive additive) is vital for the coating's homogeneity, consequently optimizing the electrochemical performance.

Lignin is another promising bio-derived binder material that becomes water soluble when the phenolic hydroxy group in Figure 1 is activated at high pH¹⁷. Being a waste material from the pulp industry, it offers low cost, and high abundance^{18,19}. It has been researched as a precursor in the production of several battery components¹³, including the separator, conductive additive, activated carbon for capacitors²⁰, electrolyte²¹, and binder material^{3,22–25}. The lignin molecule is complex and consists of the monolignol monomer species shown in Figure 1^{19,26}. The molecular characteristics depend on the pre-treatment method (kraft, soda, or steam exploded) and whether it is derived from softwood (poplar) or hardwood (pine). The molecular masses and glass transition temperature (*T_g*) of lignin isolated from different resources have been reported to be in the range of 1000 - 20 000 g/mol, and 91 - 174 °C, respectively^{19,27}. Additionally, it has a higher electrical conductivity than the commercial PVDF binder.

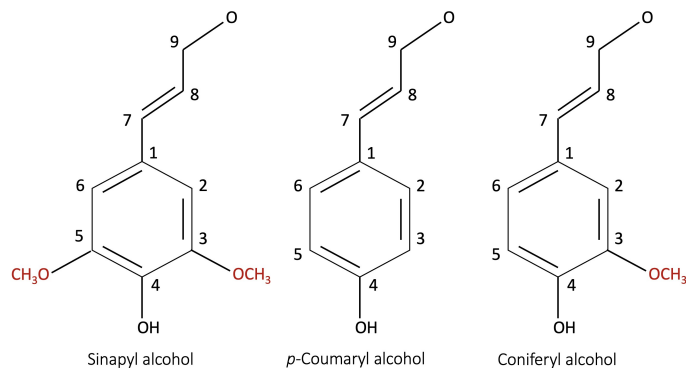


Fig. 1 The monomer species building up a lignin molecule: (a) p-coumaryl alcohol (4-hydroxyl phenyl, H), (b) coniferyl alcohol (guaiacyl, G), (c) sinapyl alcohol (syringyl, S)^{19,26}

Lu *et al.*²² studied lignin as a binder material for the aqueous production of LFP cathodes and graphite anodes and reported a high reversible capacity of 148 and 305 mAh/g, respectively. Pore removal through calendaring decreased the cathode's specific capacity due to polarisation²². They also emphasized the need for a pre-treatment of the lignin to remove small molecular structures which supposedly diffused into the electrolyte.

Ponnuchamy *et al.*²³ recently compared the binding ability of lignin, other sustainable cellulose-based binders, and unsustainable binders to graphene sheets. Subsequently, and independently of this work, they reported that lignin offered the highest binding strength amongst all the most common binders. This makes lignin a suitable binder for both the graphite anodes and the cathodes due to the presence of the conductive carbon additive in the latter. Others¹⁰ have reported that the CMC binder binds stronger to the Al current collector than the PVDF binder. Meanwhile, little research is conducted on lignin's binding ability to the active cathode materials or the Al current collector. However, a protective carbon-coated Al (C-Al) current collector may provide strong adhesion between the current collector and lignin-based electrode coating^{8,13}. Such carbon coating may also prevent poor Al-foil wetting caused by the high surface tension of water²⁸ and protect the Al against corrosion^{8,13} during the casting step of an aqueous slurry⁸.

1.2 Solvent Evaporation and Crack Propagation

When replacing the NMP with water, the slurry's wettability to the Al-foil during coating decreases, creating an electrode coating with lower adhesion and more extensive cracking. According to Du *et al.*²⁸, this is caused by the high surface tension of water (72.80 mN/m, 20 °C) compared to NMP (40.79 mN/m, 20 °C). During solvent evaporation, a high capillary pressure build-up leads to crack



propagation in the electrode coating^{9,28}. Others claim that the extensive cracking of the aqueous processed cathode coatings is a result of H₂ release during drying, owing to the corrosion of the Al current collector²⁹. Man and Russel³⁰ found that the critical pressure for crack onset increased with decreasing electrode thickness. Zheng *et al.*³¹ reported that mechanical issues increased proportionally to the coating thickness of NMC111 and LFP cathodes.

Moreover, Buss *et al.*³² reported that dissolved or dispersed non-volatile species with a larger density than the volatile solvent can migrate during the solvent evaporation and form a "sediment" layer at the electrode surface. Inhomogeneity decreases the adhesion strength of the coating and; consequently, its electrochemical performance. This can be avoided by implementing a two-stage NMP evaporation process³³ or lowering the drying temperatures²⁸. Therefore, electrode drying should be carefully considered to avoid cracking and particle migration during solvent evaporation.

Crack propagation and fractures in the electrode coating result in poor mechanical strength, isolation of active materials, and disruption of the electronic and ionic conductive network. During cycling, the cracks in these mechanically weak coatings will further propagate and create new surfaces. This allows for more electrode-electrolyte side reactions, further growth of the cathode electrolyte interphase (CEI) or solid electrolyte interphase (SEI) surface layers, and surface phase transformations in the NMC111 (from layered R $\bar{3}m$ to disordered spinel F $\bar{3}m$ and NiO rock salt Fm $\bar{3}m$ structure), and dissolution of TMs^{28,34}. This inevitably manifests as impedance growth and capacity deterioration over multiple cycles^{34,35}. It should be mentioned that a decreasing rate capability with increased mass loading is often ascribed to the Li⁺-diffusion limitations and not necessarily crack propagation^{36,37}.

The term capacity retention varies across scientific papers^{38,39} depending on their scope of work. This work defines capacity retention as the fraction of capacity relative to the initial discharge capacity, which is useful when defining the cyclability of real devices⁴⁰.

1.3 Li-ion Leaching in Ni-Containing Cathodes

A suitable cathode chemistry for EVs is the nickel(Ni)-containing LiNi_xMn_{1-x-y}Co_yO₂ (NMC) cathodes due to its high specific capacity. However, additional challenges have been reported when transitioning to aqueous processing of Ni-containing cathodes such as LiNi_{0.33}Mn_{0.33}Co_{0.33}O₂ (NMC111) and LiNi_{0.8}Mn_{0.1}Co_{0.1}O₂ (NMC811)⁴¹. During moisture exposure, active oxygen (O) species are generated at the particle surface. These combine with water

(H₂O) and carbon dioxide (CO₂) before they further react with Li⁺ to form Li hydroxide (LiOH) and eventually Li carbonate (Li₂CO₃) species at the NMC particle surface^{41,42}. Upon water exposure during the slurry processing step, the Li⁺ leach out from the NMC111 surface as displayed in Figure 2, leaving the outer layers delithiated.

The mechanism related to the charge compensation following the Li⁺-loss in the near-surface region of the NMC111 is disputed in the literature²⁹. Two scenarios have been widely discussed; one suggesting the spontaneous reduction of Ni³⁺ to the more thermodynamically stable Ni²⁺⁴³, and the other suggesting a H⁺/Li⁺-exchange mechanism illustrated in Figure 2^{29,44}. The reduction of Ni-ions is aggravated in more Ni-rich NMC cathodes as the ratio between Ni³⁺/Ni²⁺ is high, and recent articles suggest that this type of charge compensation occurs upon long-term humidity exposure (over several months), whereas the H⁺/Li⁺ exchange is dominant during the initial stage of exposure to humidity or water²⁹.

Zhang *et al.*⁴⁵ exposed NMC111 particles to water and humidity (ambient atmosphere, 20 °C, 50 % relative humidity) and reported that the Li⁺-leaching took place the first 15 minutes, forming a 10 nm thick surface layer of LiOH and Li₂CO₃. The humidity-exposed NMC111 was cycled in coin cells (versus a Li-metal anode), and the capacity decreased with 10 mAh/g at 1C. The initial discharge capacity and the capacity retention after 30 cycles were 139 mAh/g and 95 %, respectively. This capacity loss was confirmed by Cetinel *et al.*¹⁶ during aqueous production of NMC111 tested in full cells using graphite as an anode.

On the other hand, Jung *et al.*⁴³ reported that a 10 nm thick surface layer was found on humidity-stored Ni-rich NMC811; however, no significant changes were detected on the NMC111 surface. Shkrob *et al.*⁴⁴ reported that the initial capacity loss from Li⁺-leaching was regained during the first few cycles. Doberdo *et al.*⁸ also detected an initial capacity decrease, but explained that this was likely caused by the corrosion of the Al current collector since the dissolution of LiOH and Li₂CO₃ raised the slurry pH above the stability window of the Al-foil (pH = 4.5 - 8.5).

This report investigates lignin as an alternative binder material for the aqueous processing of NMC111 cathodes. Firstly, we gradually replace the standard PVDF/NMP binder/solvent with lignin/NMP, resulting in four cathode coatings with a PVDF:lignin binder ratio of 100:0, 75:25, 50:50, and 0:100. Thereafter, the NMP solvent is replaced with water, and CMC/lignin or lignin are tested as binders. The electrochemical and thermal stability of lignin is revealed through cyclic voltammetry (CV) and differential scanning calorimetry (DSC), respectively. The slurry rheology for different powder (NMC111:binder:CB) to liquid



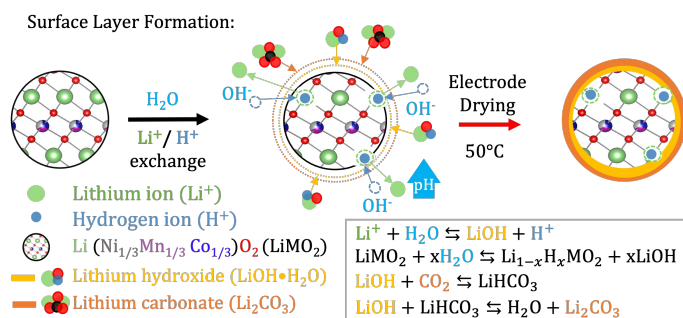


Fig. 2 When the NMC material is exposed to water Li^+ starts leaching out from its structure while H^+ from the water intercalates the structure⁴⁴. OH^- in the solution steadily increases the pH and combines with Li^+ to form LiOH as the water evaporates during electrode drying. Further, LiOH reacts with CO_2 to form LiHCO_3 and eventually Li_2CO_3 .

(NMP or water) ratios (P:L) are measured to reveal the dispersion network and ensure a proper viscosity for the coating. Furthermore, two different drying temperatures (50 °C and 90 °C) and doctor blade coating thicknesses (150 μm and 200 μm), calendaring pressures, and carbon-coated Al-foil (C-Al) are tested, aiming to obtain a coating with high mechanical strength. The electrochemical performance of aqueous-produced cathodes using CMC/lignin or pure lignin as binders are compared to PVDF/NMP-based cathodes at high discharge C-rates (5 C) and over 100 cycles.

2 Experimental

Table 1 presents an overview of all parameters tested during the slurry fabrication and coating. This includes binders, solvents, different NMC111:CB:binder ratios, wet coating thickness, and current collectors. The slurry viscosity, electrochemical and thermal stability, surface cracking, binder migration, mechanical strength, specific capacity, and capacity retention were measured.

2.1 Cathode Preparation

Three pre-mixed binder:liquid solutions of (PVDF:NMP (1:20 wt %), lignin:NMP (1:10 wt %), or lignin:(water+10wt% ethanol) (1:10 wt %) were stirred with a magnetic stirrer overnight at 40 °C to dissolve the binder. Detailed on the chemicals used are presented in Table S1. The dissolved binder was mixed with NMC111 (Targray) and carbon black (CB) (Imerys and Carbon, C45) to a wt% of NMC111:CB:binder and additional solvent to reach a specified powder:liquid wt % (P:L). The slurry chemistry ratio, binder(s) chemistry, electrode drying temperature (°C), current collectors, and doctor blade gap for tape-casting are presented in Table 2.

A non-contact planetary mixer was used for the slurry mixing (THINKY ARE250CE). The NMP/PVDF-based slurries were mixed at 1500 rpm for 25 minutes (min), followed by 2000 rpm for 5 min. The water-based slurries pre-mixed the binder and CB for 10 min at 1000 rpm, 2000 rpm, and 1000 rpm, respectively, before the NMC111 was introduced and the mixing procedure was repeated. The rheology and pH of these slurries were measured.

The slurries were coated onto an Al-foil or C-coated Al-foil (C-Al) with a doctor blade gap of 150 or 200 μm using a tape caster (MSK-AFA-HC100, MTI Corp.). The electrodes were dried at 50 or 90 °C overnight in a vacuum, calendared (Electric Hot Press, MSK-HRP-01, MTI corp.) at different gap sizes (40, 45, 60, or 80 μm) four times, and punched to 15 mm diameter discs (MSK-T-12, MTI Corp.). The dried electrodes were weighed, the thickness was measured before and after calendaring using a micrometer (VWR \pm 0.001 μm), and the resulting porosity was calculated from the material densities with the equation 1 in⁴⁶. The theoretical material densities used for NMC111 (Targray), CB (Imerys), lignin (Sigma Aldrich), and PVDF (Sigma Aldrich) were 2.3, 1.9, 1.3, and 1.8 (g/cm³) at 25 °C, respectively.

The coated electrodes were stored in a desiccator filled with silica gel and post-dried at 120 °C for a minimum of 4 h to remove moisture before being introduced to an argon-filled glove box ($\text{O}_2 < 0.1$ ppm, $\text{H}_2\text{O} < 0.1$ ppm) for coin half-cell (CR2032, MTI Corp.) assembly. Pre-cut Li-metal chips (15.6mm*0.25mm diameter*thickness), 99.9 %, Xiamen Tmax Battery Equipment) were cleaned to remove surface impurities and used as anode for the coin half-cells. A polypropylene (Celgard 2320) disc (17 mm diameter) was used to separate the coated cathode and the Li-metal anode. A pre-made salt solution of 1 M lithium hexafluorophosphate (LiPF_6) dissolved in ethylene carbonate/ethylmethyl carbonate/diethyl carbonate (EC:DMC:DEC 1:1:1, Sigma Aldrich) was used as the electrolyte. 20 μL was subjected to each side of the separator to ensure proper wetting. To achieve good contact and obtain uniform current distribution, a stainless steel spacer and spring were placed on top of the Li-metal anode before crimping the cell (MSK-PN110-S, MTI Corp.) by applying a pressure of 120 psi.

2.2 Characterisation Methods

2.2.1 Raw Material Characterisation

Differential scanning calorimetry (DSC) and cyclic voltammetry (CV) were used to test lignin's thermal and electrochemical stability, respectively. The CV was performed on different coatings against a Li metal in coin cells using a Bi-



Table 1 The different binders, slurry composition ratios (wt% of the NMC111), solvents (L), electrode drying temperature (DT), powder:liquid ratio (P:L), plain aluminum (Al) or carbon-coated (C-Al) current collector (CC), and doctor blade coating gap (DBG) for the electrodes tested.

Solvent	Binder(s) [wt %]	NMC111:CB:binder [wt %]	DT [°C]	P:L [wt %]	CC	DBG [μm]
NMP	PVDF:Lignin					
	100:0	85:10:5	90	1:2	Al, C-Al	150, 200
	75:25	85:10:5	90	1:2	Al	150
	50:50	85:10:5	90	1:2	Al	150
	0:100	85:10:5	90	1:2	Al	150
	0:100	85:10:5	50	1:2	Al	150
Water	0:100	80:11:9	50	1:1.7	Al, C-Al	150, 200
	0:100	90:5:5	50	1:1.3	C-Al	200
	CMC:Lignin					
	2:7	80:11:9	50	1:2.4	Al, C-Al	150, 200

oLogic VMP3 Battery Cycler between 2.8 - 4.5 V vs Li⁺/Li at a scan rate of 1 mV/s, and the corresponding current was measured. The DSC analysis was done with a DSC Q2000 (TA Instruments, USA) with Liquid Nitrogen Cooling System as a cooler. The calibration of temperature and the heat flow was conducted using indium. The heat capacity was calibrated with sapphire glass in the temperature range between -150.0 °C and 300.0 °C. According to TA's instrument recommendations, helium was used as purge gas and applied at 25.0 ml/min. The reference sample was an empty, hermetically sealed aluminum pan. The samples with masses between 6.0 mg and 12.0 mg (for conventional DSC) and 10 to 15 mg (for modulated DSC) were placed into aluminum pans with hermetic lids. The pans were sealed with a Tzero®DSC Sample Encapsulation Press (TA instruments, USA). Then the samples were placed by an auto-sampler into the DSC cell. The thermal properties were determined using the TA Universal Analysis 2000 version 4.5A software (TA Instruments, USA).

The conventional DSC scanning used for lignin was conducted in one step. The samples were equilibrated at 30.0 °C for 5 min and heated up to 200 °C at a rate of 10.0 °C/min. The modulated DSC (MDSC) procedure used for the PVDF sample was used to clarify thermal processes in polymers. The modulation amplitude was ± 1.0 °C/min, and the heating rate was 3.0 °C/min. The MDSC method helped clarify the melting and re-crystallization processes and glass transition. This method measured the differences in heat flow between a sample and a reference as a function of time and temperature, but the heating profile differed from conventional DSC. The sample temperature continuously increased with time but in a sinusoidal trend. The total heat flow could therefore be split into the heat capacity component (reversing heat flow) and kinetic component (non-reversing heat flow)⁴⁷. The reversing heat flow

denoted the melting and glass transition, while the non-reversing heat flow denoted the recrystallization or crystalline structure perfection. The comparison between the reversing and non-reversing heat flow allows the splitting of the exothermic recrystallization peaks when overlapping the endothermic melting peaks or glass transition.

The onset (T_o) and end (T_e) points of melting was defined as the temperature at which a change in the slope of the heating curve occurs. It should be noted that the glass transition in some substances like cellulose and polymers can be weak. Thus, the inflection point (T_i) was determined as a negative peak of the derived heat flow curve. The melting energy was obtained by integrating the DSC melting peaks (the linear baseline function integration), and the glass transition was determined with TA Universal Analysis 2000 version 4.5A software (TA Instruments, USA) and characterized by the T_o , T_e , and T_i .

2.2.2 Rheology Measurements

A rheometer (AR-G2, TA Instruments Trios V2.6) with a 40 mm parallel plate geometry at 22 °C was used to test the rheology of the slurry. The test was carried out using a steady-state flow mode followed by an oscillatory mode. The viscosity of the slurry was measured using a linear sweep with an increasing shear rate from 1-70 1/s in the steady-state flow mode. The storage modulus (G') and loss modulus (G'') were measured with an increasing angular frequency (680-1 rad/s) in the oscillatory mode. The slurries that were not tested directly after mixing were remixed at 2000 rpm for 10 minutes in a planetary mixer (Thinky-Mixer ARE-250). A 30-second equilibrium soak time was set before the rheology experiment for the slurry to achieve the correct temperature (22 °C) and reach equilibrium.



2.2.3 Scratch Test and Pen Test

A micro scratch tester (MST, Anton Paar) was used to investigate the effect of calendaring on the mechanical properties of the cathode surface. A linear progressive scratch test was performed by placing a Rockwell diamond indenter on the cathode coating surface. The non-calendered cathodes had increasing loads from 30 - 200 mN applied, with a loading rate of 28.33 mN/min for a 3 mm scratch. For the calendered cathodes, the load applied increased from 30 - 500 mN, with a loading rate of 94 mN/min for a 5 mm scratch. A pen test, which works as a simplified T-bend test commonly used for coatings, was conducted to test the cathode coating's mechanical strength by bending the cathode sheet around a pencil with a diameter of 0.5 cm. They were mechanically strong if they resisted cracking when exposed to bending.

Cyclic voltammetry (Biologic BCS-805) was used to investigate the electrochemical stability of the Al-foil, carbon-coated Al (C-Al), carbon black, and carbon black/lignin (50/50 wt%) in coin cells with Li as a counter electrode (two-electrode configuration) and scanned between 2.8 V - 4.5 V vs. Li⁺/Li using a sweep rate of 1 mV/s. The carbon black and lignin/carbon black were mixed with water in a 1:1.3 powder:liquid ratio using the frame procedure for the slurry mixing and coated onto a C-Al using a 150 μm doctor blade gap. This resulted in a 30 μm thick carbon black coating with a mass loading of 2.9 mg/cm², and a 20 thick lignin/carbon black coating with a mass loading of 10.6 mg/cm².

2.2.4 SEM/EDS

Scanning electron microscopy (SEM) was used to investigate the electrode coating's microstructural morphology and topography. The SEM imaging was performed using a Zeiss Ultra 55 apparatus with a working distance (WD) of 10 mm and an Everheart-Thornley Secondary Electron Detector. The accelerating voltage was 10 kV with a scan time of 20.2 seconds per image. ImageJ (version 1.52a) was used to analyze the particle migration. An Bruker XFlash EDX detector was used for EDS mapping at a working distance of approximately 10 mm and an accelerating voltage of 15 kV. The mapping was conducted over the electrode surface for 10 minutes (magnification 200x). Bruker software (Version 1.9) was used for elemental mapping analysis.

2.2.5 XPS

The X-ray photoelectron spectroscopy (XPS) was conducted on dry NMC111 powders to reveal the surface composition of pristine NMC111 particles after being stored (1 year) in dry argon atmosphere (A), humid air (B), and mixed in distilled water for 24 hours (C). The samples

were mounted onto an indium foil and dried in a vacuum oven overnight at 120 °C. The sample analysis chamber pressure was 1·10⁻⁹ Torr during the operation. Elemental maps were collected with a pass energy of 160 eV with two sweeps, using a monochromatic Al Kα source (15 mA, 12 kV). High-resolution regional acquisitions were performed with a pass energy of 20 eV with eight sweeps and 0.1 eV step size for each element.

2.3 XRD

The XRD measurements were performed on a Bruker D8 DaVinci Diffractometer using a Cu Kα radiation (λ = 1.54 Å) source, and a fixed slit size of 0.2. The XRD scan was scanned between 2θ values of 10° to 80°. The analysis of the XRD profiles was performed using DIFFRAC.EVA software (Bruker). The reference scans used for matching were found in PDF 2019+ database, and are found in Table S4.

The Rietveld refinement was used for structural analysis and performed on DIFFRAC.TOPAS (V5.0, Bruker AXS). They were based on a rhombohedral α-NaFeO₂ structural model, with R $\bar{3}m$ space group and Li placed in the 3a position, Ni, Mn, and Co in the 3b position, and O in the 6c position. The refinements assumed fully stoichiometric samples and a model in which Li and Ni were free to switch positions (cation mixing) while Mn and Co were confined to the TM layer. The a and c lattice parameters and the Oz coordinate were treated as variables. The line widths were modeled within the fundamental parameters approach assuming microstrain-type broadening.

2.3.1 Electrochemical Performance

The coin cells were tested galvanostatically using a Lanhe potentiostat (CT2001A) at a controlled temperature (19 ± 1 °C). The cells were cycled against a Li metal anode between 3.0 - 4.3 V versus Li⁺/Li. During discharge, a constant current (CC) was applied. During charge, the CC was followed by a constant voltage (CV) at 4.3 V until the current reached < C/10. The cells underwent between 3 to 5 formation cycles at C/10. During the rate test, the discharging C-rates increased after every 5th cycle (C/10, C/5, C/2, 1C, 2C, 2.5C, 3C (or 5C), and C/10; 1C = 160 mA/g), while the charging C-rate remained constant at C/2. To investigate the long-term cyclability, the cells were cycled at a constant rate (C/2) for 100 cycles.

3 Results and Discussion

Since little research has been conducted on cathode fabrication using lignin as a binder, this article aims to give the reader a holistic overview of the optimal fabrication parameters needed to obtain an electrochemical performance comparable to that of commercialized PVDF binders.




The four different binder compositions tested (PVDF (85:10:5), PVDF/lignin (85:10:5), and CMC/lignin (80:11:9) and lignin (80:11:9 and 90:5:5) shown in Table 2 will be discussed in the following chapters. Different coating thicknesses, porosities, and mass loadings were tested to find the optimal cathode fabrication route. Only cathodes with comparable mass loading will be compared in the microstructural and electrochemical analysis.


A higher mass loading was obtained for all coatings when increasing the doctor blade gap (DBG) during tape casting from 150 μm to 200 μm . The electrode's mass loading was also dependent on the NMC111:CB:binder composition ratio and binder chemistries used. For example, the mass loading decreased from 9.7 mg/cm^2 to 5.5 mg/cm^2 when changing the binder from pure lignin to CMC/lignin because of CMC's thickening effect. The porosity and thickness are; therefore, carefully considered and reported for each cell rather than only the final electrode density (g/cm^3). This is especially important when considering the rate capability, as this is kinetically limited by the coating's electronic- and ionic conductivity³⁶.

The calendering process decreased the porosity at the expense of thickness and made the coatings more uniform as indicated by their lower standard deviations. A small calendering gap (40 - 45 μm) resulted in high pressures (P_{high}) which extensively reduced the porosity. A medium calendering pressure (P_{medium} , 60 - 80 μm gap) generally resulted in a higher porosity. It should be mentioned that porosity of 0 % was defined according to the formula in Equation 1 and the complete removal of pores was unlikely.

Table 2 sums up the initial discharge capacity (IDC) of the cathodes measured through galvanostatic cycling at C/10. The PVDF/NMP-based cathode obtained the specific capacity (154 mAh/g) expected from the Targray supplier ($\sim 150 \text{mAh}/\text{g}$). Large variations were detected for the lignin-based cathodes depending on the binder (lignin or CMC/lignin), solvent (NMP or water), and current collector (C-Al or Al). The reasons for these discrepancies will be discussed below. An interesting trend is that the lignin/water-based cathodes calendered under P_{medium} pressures generally showed a higher initial capacity than the uncalendered or calendered with high pressure, suggesting that P_{medium} provided a good combination of electronic conductivity and high porosity. It should also be mentioned the uncalendered lignin/water-based cathodes coated onto pure Al may suffer from larger errors in the measured IDC, since the cutting of these cathodes resulted in more material loss from the edges, Figure S2b.

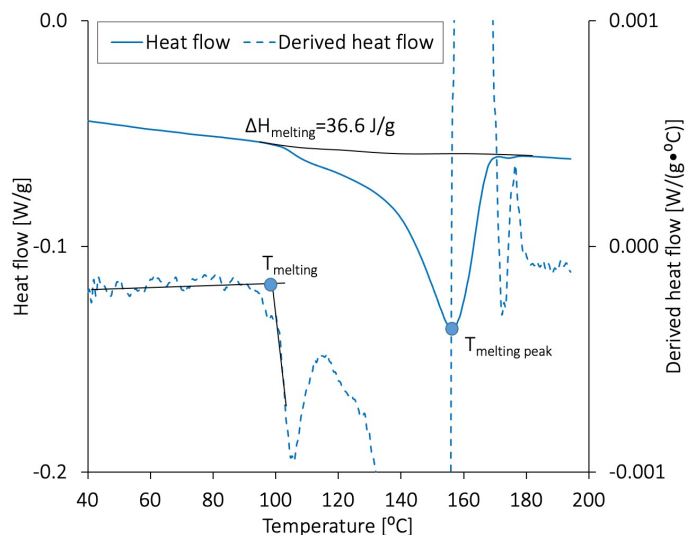

(a) Modulated DSC scan of PVDF.

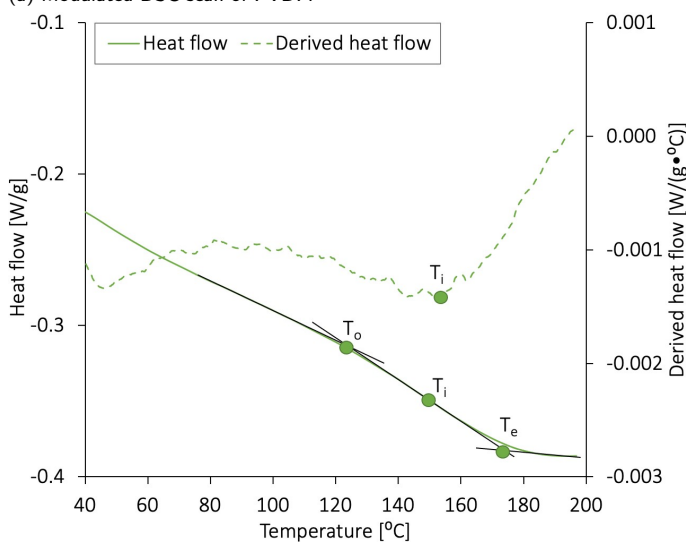

(b) DSC scan of lignin.

Fig. 3 Differential scanning calorimetry measurement (DSC) of the (a) PVDF and (b) lignin raw materials between 30 - 300 $^{\circ}\text{C}$. $\Delta H_{\text{melting}}$ = heat of fusion, T = temperature, T_o = onset, T_i = inflection, T_e = end.

3.1 Thermal Stability of Binders

The electrode materials should have high thermal stability to avoid degradation or mass loss during cell fabrication and operation. Cho *et al.*⁴⁸ performed a DSC analysis on different NMC materials and found that the NMC111 is thermally stable below 223 $^{\circ}\text{C}$. Al-Shroofy *et al.*⁴⁶ used a thermal gravimetric analysis (TGA) and found that PVDF and CB did not undergo mass loss until reaching temperatures of 400 - 460 $^{\circ}\text{C}$ and 500 - 600 $^{\circ}\text{C}$, respectively. Loeffler *et al.*⁴⁹ reported that CMC was not affected by thermal treatments below 200 $^{\circ}\text{C}$.

A DSC analysis revealing the thermal stability of PVDF and lignin is presented in Figure 3a and Figure 3b, respec-



Table 2 A detailed list of the solvent, cathode binders, doctor blade coating gap (DBG) and calendering gap (CG), dry coating thickness, and porosity before(b) and after(a) calendering, mass loading (ML), initial discharge capacity (IDC) at C/10, and current collector (CC). The NMC111:CB:binder wt % was 80:11:9, *85:10:5 or ^a90:5:5. The drying temperature T=50 °C (water) and 90 °C (NMP) unless specified.

Solvent	Binders [wt %]	DBG/CG [μm]	Thick. b/a cal. [μm]	Por. b/a cal [%]	ML [mg/cm^2]	IDC [mAh/g]	CC	Plot	
NMP 90 °C	PVDF:Lignin							-	
	100:0*	200 / 45	63±7 / 33±3	53±4 / 9±1	6.6±0.6	150	C-Al	Figure S9a	
	100:0*	200 / 45	54±4 / 40±3	56±4 / 30±3	6.1±0.8	154		Figure S9a	
	75:25*	150 / 45	43±6 / 28±3	53±6 / 27±4	4.4±0.2	153	Al	Figure 8	
	50:50*	150 / 45	50±1 / 39±1	57±1 / 25±4	4.8±0	132		Figure 8	
	0:100*	150 / 45	42/-	51/-	4.4	83		Figure 8	
	0:100* (50 °C)	150 / 45	49 / -	57 / -	4.5	141		Figure 8	
	0:100 (90 °C)	150 / 45	74±5 / 17	71±14 / -	4.7	128		Figure 8	
	Water 50 °C	0:100	200 / 45	80±5 / 41±2	44±1 / 0±16	9.7±0.2	120/125	C-Al	Figure 10c
		"	200 / 60	77±11 / 42±2	40 / 16±5	"	136		Figure 10c
"		200 / 80	77±11 / 64±2	38 / 32	"	148	Figure 10c		
0:100		150 / 45	74±9 / 40±4	46±7 / 15±1	7.4±0.3	143/127	Figure 10b		
"		150 / 60	65±15 / 34±5	44 / 22±17	"	125	Figure 10b		
"		150 / 80	72±3 / 54±3	50 / 37	"	139	Figure 10b		
0:100 ^a		200 / 80-60	/ 62±3	/ 31	7.5±0.2	154		Figure 12	
CMC:Lignin								-	
2:7		200 / 40	45±3 / 36±1	46±1 / 32±2	5.1±0.4	147 / 151	Al	Figure 9	
2:7		200 / 40	46±2 / 35±1	44±2 / 19±2	5.6±0.2	135 / 142		Figure 9	
"	200 / 60	55±3 / 47±3	51±0 / 10±0	"	141	C-Al	-		
"	200 / 80	55±3 / 46±3	51±1 / 21±1	"	143		-		
"	150 / 60	45 / 41±3	51±0 / 27±1	4.5±0.2	-		-		
"	150 / 80	45±1 / 41±2	53±2 / 30±4	"	150/151		-		



tively. The melting peak of lignin was found at 152 °C, and the glass transition temperature (T_g) expected for the amorphous kraft lignin was 124-174 °C^{19,22}. According to Figure 3a, PVDF had a wide melting temperature with the melting peak at 156 °C, and the heat of fusion ($\Delta H_{\text{melting}}$) was 36.6 J/g. By using the $\Delta H_{\text{melting}}$ for a 100 % crystalline PVDF (104.7 J/g⁵⁰), the crystallinity of the PVDF was calculated to be 35 %. The crystallinity and melting temperature for PVDF usually vary between 35 - 70 %⁵⁰ and 150 - 177 °C, respectively.

The drying temperature used for cathode vacuum drying at laboratory-scale is generally between 80 - 130 °C^{3,51-54}. The solid components used in these cathodes are; therefore, expected to be thermally stable within the temperature range used in this report (50 - 120 °C). The PVDF partly melted during the post-drying step at 120 °C; however, such thermal activation has previously been reported to increase the bonding strength between PVDF, NMC, and CB and maintain the electrode's porosity in dry-coated electrodes⁵⁵.

3.2 Electrochemical Stability of Al, Carbon, and Lignin

Cyclic voltammetry (CV) is used to investigate the electrochemical stability of the aluminum (Al) current collector, the carbon-coated (1 μm) Al current collector (C-Al), a 2.9 mg carbon black (CB) coating (20 μm thick) on C-Al, and a 10.6 mg CB/lignin (50/50 wt %) coating (30 μm thick) on C-Al. The resulting scans are presented in Figure 4 and Figure S14. Lignin was mixed with CB as it has an absolute low conductivity. The current peaks (I_p) increased with the amount of CB and lignin present, indicating that these species underwent oxidation and reduction (redox) reactions within the potential window of 2.8 - 4.5 V. The Al current collector in Figure S14a underwent an irreversible oxidation reaction at 4.2 V which contributed to a oxidation current peak (I_{p0}) of 55 μA at cycle 8, before the oxidation reaction diminished. The same trend was detected for the C-Al-foil in Figure S14b; however, the additional 1 μm carbon coating increased the I_{p0} by 10 μA . Additionally, the carbon contributed to a reduction reaction at around 4.1 V.

When increasing the carbon content by coating the C-Al with ~ 2.9 mg CB in Figure 4a, there was no peak shift which indicated that the same redox reactions took place, but the I_{p0} of the first cycle increased with 50 μA . Thus, the CB contributed with ~ 17.2 $\mu\text{A}/\text{mg}$ to the oxidation peak at 4.3 V during the first cycle. The CB underwent its most extensive oxidation reaction during the initial cycle, and the I_{p0} declined steadily with cycle number.

When introducing lignin into the system by coating the

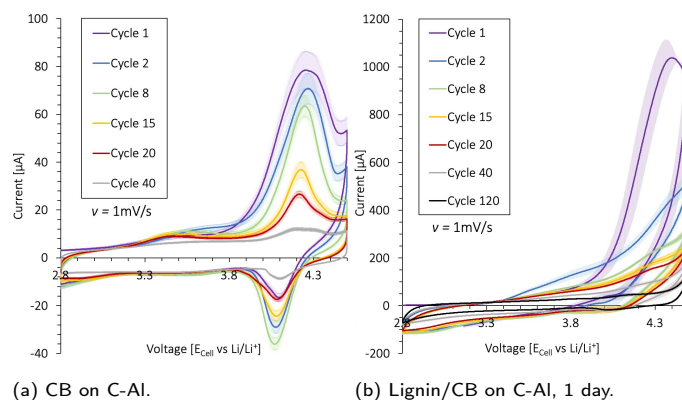


Fig. 4 The electrochemical activity of the a) carbon black (CB) coated on C-Al, and lignin/CB (50/50 wt %) coated on C-Al scanned after 1 day wetting. The coin cells were scanned between 2.8 - 4.5 V (vs Li/Li⁺) using a Li-metal anode, LiPF₆ in ED/DMC/DEC electrolyte, and a scan rate of $v = 1$ mV/s at 22 °C.

C-Al with a 10.6 mg CB/lignin (50/50 wt %) coating, there was a pronounced increase in the overall oxidation current in Figure 4b and Figure S14c. The I_{p0} shifted to >4.3 V insinuating that lignin underwent different oxidation reactions than the CB. However, during the first cycle, the I_{p0} for CB and lignin was found at 4.3 V. By deconvoluting the CB current during the first cycle (~ 17.2 $\mu\text{A}/\text{mg}$), lignin contributed to 10 times the amount of current per mass (~ 172 $\mu\text{A}/\text{mg}$). The I_{p0} was halved for the second cycle, accompanied by a peak shift to 4.5 V, which was above the typical upper cut-off voltage for NMC cathodes used for galvanostatic cycling. During the following cycles, all peak currents slowly diminished and the oxidation reaction stabilized. There was also a reduction reaction taking place with a peak height at 2.8 V, but also this current decreased over subsequent cycles. The results insinuate that the redox side reactions between the lignin and electrolyte were large during the first cycle, but subsided upon cycling.

When incorporating lignin in a cathode and cycling this galvanostatically in a coin cell against Li metal, the apparent oxidation side reaction in the first cycle may be visible at high voltages during the first charge cycle, while the reduction reaction would appear at low voltages during discharge. In fact, the prominent initial irreversible oxidation reaction of lignin conceivably contributed to the elongated voltage profile > 3.8 V and the high initial charge capacity during the first formation cycle of an 80:11:9 lignin/water-based cathode in Figure 13.

There was no apparent trace of these side reactions after the first charge cycle in the voltage curves. The irreversible side reactions stabilized over subsequent cycles according to the CV, and the discharge curve originated to its ex-



pected NMC shape; thus, they did not appear to impede the overall capacity contribution after the first formation cycle. However, coulombic efficiency (CE) can be used to determine the efficiency of Li^+ -(de)intercalation and is a sign of irreversible side reactions. The average CE over 100 cycles at C/2 was generally lower for all lignin/water-based cathodes (96.6-98.2 %) compared with the PVDF/NMP-based cathodes (99.2 %) (Figure S13). Thus, the charge capacity was higher than the discharge capacity suggesting which may suggest that additional oxidation reactions took place.

Since the mass loading of lignin for the CV scans was relatively high ($\sim 5.3 \text{ mg/cm}^2$) compared to the content in the cathodes ($0.4\text{-}1.0 \text{ mg/cm}^2$), the side reactions associated with lignin were 5-13 times lower than in the CV scan depending on the NMC111:CB:binder ratio and the mass loading of the cathode. Although they may be associated with the sodium (Na) or sulfur (S) in the lignin (EDS and XRD in Table S2 and Figure S16b), investigation on the mechanism behind these redox-reactions is outside the scope of this study.

As there was no apparent change in the reactions after a longer electrolyte exposure time (6 days in Figure S14c), these side reactions were likely not causing the capacity drop seen in the first cycles in Figure 12. This drop is likely due to poor wetting of the electrodes as explained in subsection 3.6.2.


3.3 Slurry Rheology

Rheology measurements were conducted on the NMP- and water-based slurries to reveal the optimal powder:liquid (P:L) ratio needed to obtain a proper viscosity for the tape casting, Figure 5.

The linear sweep measurement in Figure 5a showed that the viscosity decreased with an increasing solvent and shear rate (1/s). For the 85:10:5 PVDF/NMP-based slurries, a 1:2 P:NMP ratio provided the optimal viscosity for tape casting. For the 80:11:9 lignin/water-based slurries, a 1:1.7 P:water ratio resulted in the same optimal viscosity. This was attributed to the lower viscosity of water compared to NMP⁵⁶, and the additional 1 wt % CB in the lignin/water slurry (80:11:9) relative to the PVDF/NMP slurry (85:10:5). Since 50 % of the drying time is used to extract the last 10 % of the solvent, the solvent reduction will not significantly affect the energy consumption used for evaporation during drying⁵⁷, and the elimination of the NMP recovery step will therefore be the main contributor.

The oscillatory mode test in Figure 5b are used to reveal the interaction between PVDF binder, NMC111, and CB through the storage modulus (G') and loss modulus (G'')⁴⁶. The NMP/PVDF-based slurries with a powder:liquid ratio

of 1:2 and 1:2.5 showed a liquid-like behavior ($G' < G''$), whereas the 1:1.5 slurry showed gel-like behavior ($G' > G''$). In agreement with Al-Shroofy *et al.*,⁴⁶, these gel-like properties are undesirable for slurry tape casting. This agreed with these results as the 1:2.5 slurry resulted in poor mixing and an uneven slurry coating. The lignin/water 1:1.7 and PVDF/NMP 1:2 slurry behaved almost identically during the oscillatory test, both having favorable liquid-like behavior.

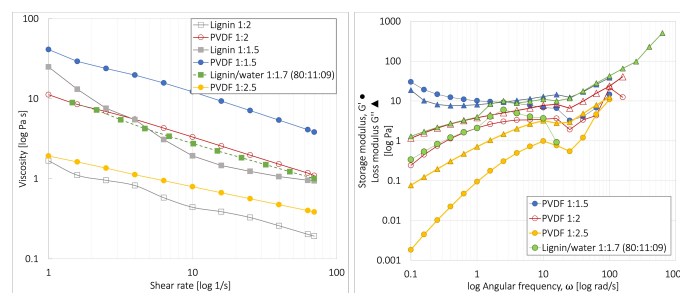

(a) Linear sweep.

(b) Oscillation measurement.

Fig. 5 Rheology measurement revealing the viscosity for lignin/water or PVDF/NMP based slurries with different powder(NMC111:CB:binder):liquid (P:L) ratios. Unless specified, the powder ratios are 85:10:5 wt % (relative to wt % NMC111). a) shows the linear sweep with increasing share rate from 1-70 1/s. b) Show an oscillation measurement angular frequencies 680-1 rad/s revealing the storage modulus (G' , ●), and loss modulus (G'' , △).

3.4 Micro-structural Analysis

The commercial cathode fabricated using PVDF/NMP as binder/solvent was gradually replaced with lignin/NMP, and entirely replaced with lignin/water. The cathodes were dried at 90 °C or 50 °C in a vacuum and the resulting binder migration, surface cracking, and particles were analyzed in SEM.

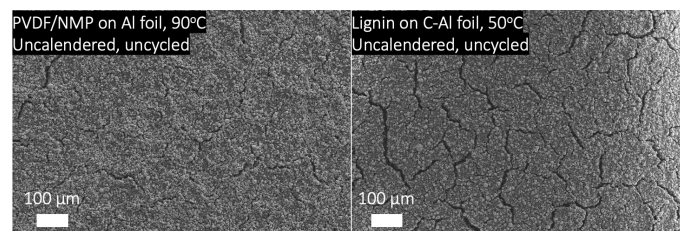


Fig. 6 SEM surface crack analysis of an uncalendered PVDF/NMP-based cathode dried at 90 °C (left) and a lignin/water-based (right) cathode dried at 50 °C with similar mass loading ($7.4 \text{ mg/cm}^2 \pm 0.2$).

The surface of lignin/NMP-based and lignin/water-based cathodes dried at temperatures of 50°C and 90°C were analyzed in SEM. The accumulation of lignin binder on



the electrode surface was classified according to the percentage of NMC111 particles covering the surface (Figure S4). An extensive surface layer (2 % NMC111 surface coverage) was detected for the lignin/NMP-cathodes due to the migration of the undissolved low-density lignin molecules. The lignin binder migration in lignin/NMP cathodes was mitigated when drying at 50 °C, revealing a 12 % NMC111 coverage, due to a low NMP evaporation rate^{22,58}. When replacing the NMP solvent with water, the lignin binder migration further diminished (19 % NMC111 surface coverage), which was close to values expected for the standard PVDF/NMP cathodes (22 %) with the same NMC:CB:binder ratio. The solubility of lignin molecules was higher in water relative to NMP, and the undissolved particles migrated more extensively during the NMP solvent evaporation⁵⁹.

The number of micro-cracks on the cathode's surface was higher for lignin/water-based cathodes compared with the PVDF/NMP-based cathodes in Figure 6. Although the cracks diminished on the surface of the lignin/water-cathodes by lowering the drying temperature from 90 °C to 50 °C (Figure S2a), more cracks were still detected when using water as solvent. Du *et al.*²⁸ also reported extensive crack formations at drying temperatures > 50 °C for aqueous processed electrodes. This was caused by the high surface tension of water relative to that of NMP, which increased the capillary pressure build-up during drying^{9,28}.

Scratch tests (Figure S3) and pen tests were used to reveal the cathode sheet's mechanical strength. Generally, the above-mentioned binder migration and cracking decreased the cathode coating's adhesion to the Al current collector and its overall mechanical strength⁶⁰.

Interestingly, all lignin-based cathode coatings delaminated from the Al current collector in flakes (Figure S2a), which indicated that lignin formed sufficiently strong cohesion forces to NMC111 and CB. This was confirmed when replacing the plain Al current collector with a carbon-coated Al (C-Al) current collector. Figure S2b shows an image of the cathode surface after cutting out the electrode discs from a PVDF/NMP cathode coated on a pure Al-foil, and a lignin/water-based cathode coated on an Al-foil or a C-Al-foil. The C-Al increased the lignin/water-based cathode's mechanical strength.

Lignin has several functional groups⁶¹, and the classification of the chemical bonds between lignin-CB-NMC111 are out of the scope of this paper and should be further investigated elsewhere^{23,62}. Additionally, the C-Al eliminated problems associated with the high surface tension of water^{63,64}, and corrosion of the Al-foil⁴⁹ during aqueous coating.

3.4.1 Calendering Pressure

Figure S2c shows that the calendering magnified the nature of the cathode's initial mechanical strength. For a lignin/water-based slurry coated onto a pure Al-foil, the coating was delaminated from the Al-foil in one large flake after calendering. Thus, the calendering intensified the poor adhesion forces between the coating and the Al-foil, and the strong cohesion between particles. For the lignin/water-based slurry coated onto a carbon-coated Al-foil (C-Al) the calendering pressure improved the mechanical strength, revealing exceptional binding abilities between lignin and carbon²³. Fewer surface cracks were observed after calendering these cathodes, and less delamination occurred during the electrode disc cutting as illustrated in Figure S5 and Figure S2b, respectively.

A SEM analysis of uncalendered and calendered cathode surfaces undergoing different calendering pressures are presented in Figure 7. These cathodes were fabricated using water as solvent and lignin as a binder and dried at 50 °C. The uncalendered cathodes show extensive surface cracking and a poor connection between the NMC111 and the CB/binder-matrix. By applying a medium ($P_{\text{medium}} = 60\text{--}80 \mu\text{m}$ calendering gap) and high ($P_{\text{high}} = 40\text{--}45 \mu\text{m}$ calendering gap) calendering pressure, the surface cracks were removed and a good NMC111-to-CB/binder matrix connection was provided. However, at the high calendering pressures (P_{high}), NMC111 particle deformation occurred. Therefore, the medium calendering pressure was preferred to provide a mechanically strong coating with good electronic conduction, while maintaining the NMC111 particle integrity.

To conclude, the reduction of surface cracks through calendering (Figure 7), drying temperature (from 90 to 50 °C), and the application of a C-Al current collector provided lignin/water-cathodes with high mechanical strength. The calendered lignin/water-cathodes using C-Al, dried at 50 °C, obtained comparable mechanical strength to PVDF/NMP-cathodes using plain Al dried at 90 °C according to pen tests²³.

3.5 Electrochemical Performance

The following section will present the electrochemical performance of NMC111 cathode coatings fabricated using the following binder/solvent systems: lignin/NMP, PVDF/NMP, (CMC/lignin)/water, and lignin/water. The use of Al-foil and C-Al-foil current collectors is also investigated.

For some of the electrodes, different mass loading and calendering pressures are tested under different discharging rates to understand the effect of electronic and ionic



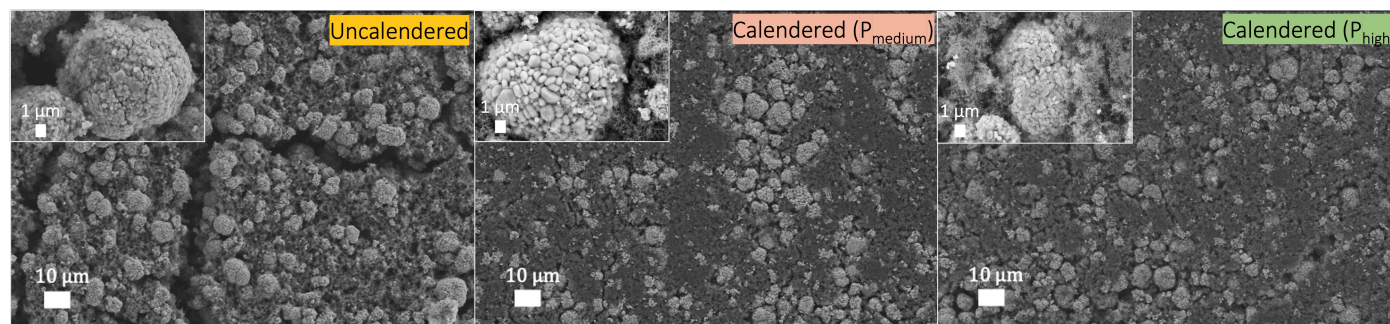


Fig. 7 SEM surface analysis of lignin/water cathode coatings with similar mass loading ($7.4 \pm 0.3 \text{ mg/cm}^2$) which was uncalendered, calendered at medium pressure using a $60 \mu\text{m}$ calendering gap (P_{medium}), or calendered at high pressure using a $45 \mu\text{m}$ calendering gap (P_{high}) (Magnitude: 1000 \times). The NMC111 particles are shown in the top right corner (Magnitude: 10000 \times). The rate capability of these cathodes is shown in Figure 10b.

conductivity on the rate performance. Lastly, different electrolyte wetting times are presented for the lignin/water-based cathodes with high (90 %) and low NMC111 (80 %) contents.

3.5.1 PVDF binder/NMP solvent

Firstly, standard PVDF/NMC-cathodes with an 85:10:5 NMC111:CB:PVDF ratio were fabricated without being exposed to humidity- or water, and used as a baseline. These cathodes showed expected initial capacity (154 mAh/g), the voltage plateau obtained the expected NMC111 shape, and was stable over 100 cycles as shown in Figure S9.

A plain Al-foil and a carbon-coated Al-foil (C-Al) current collector were tested on PVDF/NMP-based cathodes (mass loading: $6.1\text{--}6.6 \text{ mg/cm}^2$). The rate capability for uncalendered and calendered cathodes is presented in Figure S9a.

The capacity of PVDF/NMP-cathodes with plain Al-foil was similar to those reported earlier⁶⁵. The calendered PVDF/NMP cathode coated onto plain Al with 30 % porosity showed higher capacity retention at 5 C (85 %) compared to the uncalendered cathode with 56 % porosity (75 %). The low capacity at high C-rates for uncalendered cathodes caused poor electronic connections within the high porosity coating. Earlier reports suggest that the porosity for PVDF/NMP-based cathodes should be between 30-40 %⁵³ to create a coating with optimal electronic and ionic conductivity.

The application of C-Al did not impact the cell's capacity at low C-rates ($< 1\text{C}$); however, at higher rates (1 - 5 C), the capacity retention decreased for the cathodes using C-Al. The uncalendered C-Al cathode obtained 23 % of the initial discharge capacity at 5 C, compared to 69 % for the calendered C-Al cathode⁶⁶. The pen tests revealed that the C-Al current collector did not visibly improve the already high mechanical strength of the PVDF/NMP cathodes. According to the supplier of the C-Al current collec-

tor (MTI⁶⁷), the C-Al was resistant to NMP but dissolved in water. This may cause the poor compatibility of C-Al and NMP-based slurries relative to water-based slurries.

3.5.2 (Lignin/PVDF) binder/NMP solvent

The PVDF/NMP 85:10:5 cathode was gradually replaced with lignin/NMP, resulting in three different (lignin/PVDF)/NMP cathodes with different 25 %, 75 %, or 100 % lignin content. These cathodes were coated onto a plain Al-foil.

The specific discharge capacity obtained during the third formation cycle is shown in Figure 8a. The discharge capacity decreased with increasing lignin content, as the expected voltage plateau at 3.8 V seen for the baseline PVDF/NMP cathode gradually diminished due to a high overpotential. According to Figure 8b, the voltage plateau re-appeared when reducing the drying temperature from $90 \text{ }^\circ\text{C}$ to $50 \text{ }^\circ\text{C}$ or by replacing the NMP solvent with water. Thus, the capacity decreased in accord with the accumulated lignin surface layer discussed above (Figure S4).

A post-mortem SEM analysis of the (lignin/PVDF)/NMP-based cathodes (Figure S6) revealed that the accumulated lignin on the cathode surface reacted with electrolyte and created a surface layer. This not only resulted in the low capacity during the third formation cycle but also a declining rate capability (Figure S9b). We believe this layer created a barrier for Li^+ -transport which increased the intercalation resistance for cathodes with increasing lignin content when employing NMP as solvent.

Qiao *et al.*⁶⁸ also detected a surface layer on NMC111 particles in SEM after rate tests and assigned this to an unstable CEI formation associated with the LiPF_6 salt. By switching to a moist scavenger sulfonimide salt ($\text{Li}[\text{N}(\text{SO}_2\text{CF}_2\text{H})(\text{SO}_2\text{CF}_3)]$, LiDFTFSI), the surface layer was no longer detected. However, the extent of the accumulated layer detected in this report was severe in com-



parison, suggesting that the accumulated lignin on the surface was the main issue and should be avoided by properly dissolving lignin in another solvent than NMP.

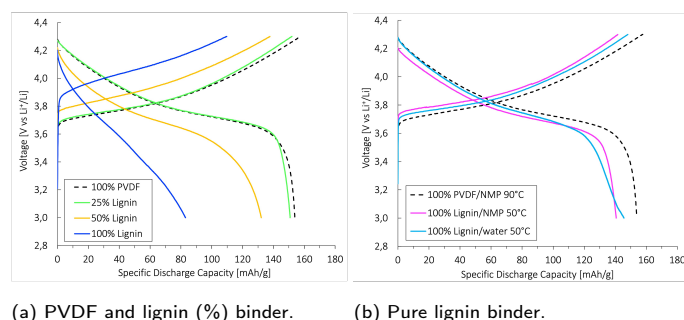


Fig. 8 Specific discharge capacity during the third formation cycle at C/10 (1 C = 160 mA/g). The cathodes were coated onto Al-foil with a mass loading of 4.4-4.8 mg/cm², and calendered at P_{medium}. A PVDF/NMP-based cathode dried at 90 °C (black) was used as a baseline. The cathodes were cycled between 3.0 - 4.3 V (vs Li⁺/Li) against a Li-metal anode in a coin cell at 22 °C.

3.5.3 (CMC/lignin) binder/Water solvent

The commercial CMC thickener commonly used for aqueous production of anodes⁴⁹ was tested in the aqueous fabrication of lignin-based cathodes to produce a CMC/lignin (2:7 wt %) cathode. Due to the very distinct effect on the viscosity of the paste, the acceptable amount of CMC was limited to 2 %⁴⁹.

The rate capability and coulombic efficiency (%) for (CMC/lignin)/water based cathodes with a mass loading between 5.1-5.6 mg/cm² are presented in Figure 9. Both a plain Al-foil and a carbon-coated Al-foil (C-Al) were tested as a current collectors. The average initial discharge capacity was between 145 to 150 mAh/g, and the capacity gradually dropped with increasing C-rates. No significant difference was detected for cathodes coated on plain Al and C-Al current collectors. At high C-rates (5 C), the capacity retention for both the Al and C-Al was as high as ~60 %. This indicated that the combination of CMC/lignin binder mix might provide sufficient electronic and ionic pathways and a proper electrical connection to the Al-foil.

The long-term cycling, rate capability, and coulombic efficiency (%) for these (CMC/lignin)/water-based cathodes are shown in Figure S12. The cathode using C-Al as a current collector obtained a higher long-term cyclability compared with the cathode coated onto a plain Al-foil. This can be explained by the larger cracks found for the water-based coatings coated on the Al-foil relative to the C-Al-foil in Figure S5, and the more extensive corrosion taking place when using plain Al-foil (Figure S7).

Pastor-Fernández *et al.*⁶⁹ systematically summed up the

aging mechanisms within a cell, and pointed to the binder decomposition, contact loss, and corrosion of the Al-foil as influential factors for impedance growth and capacity loss over multiple cycles.

We conclude that although the 2 % CMC contributed to improved adhesion to the Al for the lignin/water-cathodes, it was not enough to compensate for the poor adhesion forces between lignin and Al when exposed to volume changes over multiple cycles. This, in combination with the corrosion of the Al-foil, contributed to the decrease in the long-term cycling performance of the aqueous-produced lignin/CMC-based cathodes. Thus, a carbon-coated Al-foil was preferred as the current collector and will be used for the lignin/water-based cells presented in the next section.

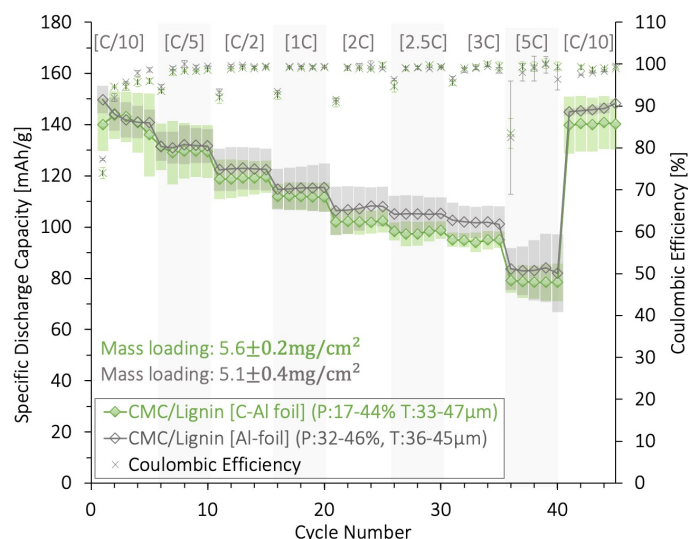


Fig. 9 The average rate capability of three cells with aqueous produced NMC111 cathodes using CMC/lignin (green diamond) coated on plain Al-foil (empty) or carbon coated-Al-foil (C-Al) (filled). T=electrode coating thickness, P=porosity. The cathodes were cycled at different [C-rates] were 1 C = 160 mA/g between 3.0 - 4.3 V (vs Li⁺/Li) using a coin cell and Li-metal anode at 22 °C. Calendered at P_{medium}.

3.6 Lignin binder/Water solvent

Figure 10 shows the rate capability of lignin/water cathodes with a mass loading of 7.4±0.4 mg/cm² (Figure 10a and Figure 10b) and 9.7 mg/cm² (Figure 10c).

Firstly, the Figure 10a shows the rate capability of the uncalendered lignin/water cathodes coated onto a C-Al-foil and an Al-foil with similar thickness and porosities. The carbon-coated Al-foil (C-Al) current collector presented high mechanical strength compared with the plain Al-foil (subsection 3.4). This created a higher electronic conductivity to the Al-foil which was crucial for the rate capability. Due to the superior rate performance and mechanical sta-



bility, all other lignin/water-based cathodes in this section were coated onto a carbon-coated Al-foil.

The capacity decrease for the Al-foil cathode could also partly be caused by the pit corrosion of the Al (Figure S7). However, the CMC/lignin in Figure 9 showed no particular difference in rate capability when comparing C-Al and Al, although corrosion also occurred for these cathodes. Thus, we believe the Al corrosion was not the main issue for a low rate performance at elevated C-rates, but rather during the long-term cycling. It is noteworthy that the lower rate capability of the lignin/water-cathodes (7.4 mg/cm²) compared to the CMC/lignin (5.1-5.5 mg/cm²) cathodes was likely caused by differences in the cathode coating's density and mass loading.

When increasing the mass loading from 7.4 in Figure 10b to 9.7 mg/cm² in Figure 10c, the rate capability decreased despite the degree of porosity. For the high mass loading cathodes, the activation time for the NMC111 particles close to the current collector increased, and the Li⁺ diffusion pathways within the cathodes were generally elongated despite having a high porosity³⁶. At a thickness > 76 μm and porosity > 43 %, the capacity retention at high C-rates (3 C) was therefore limited to 20 %.

The large standard deviations for the rate capability within each plot were likely caused by the variation in thickness and porosity for these cathodes. Generally, the lignin-cathodes with lower mass loading were less sensitive to these variations than those of high mass loading. This gives an insight into the difficulties associated with reproducing cathodes with high mass loading.

3.6.1 Calendering Pressures

Controlling the porosity through calendering is vital for a high rate of performance. High porosity is needed for a proper Li⁺-diffusion to obtain a high ionic conductivity. In contrast, a low porosity is needed to provide sufficient connections between the coated components and high electronic conductivity. The lignin/water-cathodes were calendered to different thicknesses (Table 2) to improve the electrode integrity by controlling the porosity, and strengthening the cohesion between the particles and the adhesion between the coating and the Al-foil^{53,70}.

By calendering the lignin/water-cathodes with low mass loading (7.4 mg/cm²), the porosity dropped with high calendering pressures and the rate capability of lignin/water-cathodes decreased accordingly, as illustrated in Figure 10b. Despite having a relatively high porosity (44 - 53 %), the uncalendered lignin-cathodes with low mass loading obtained a higher rate capability at 3 C (84 %) compared with the calendered cathodes (54 %).

This meant that even at a high porosity of 53 %, the

C-Al-foil enabled proper connections between the coating and the Al and that the large carbon/lignin-matrix in these 80:11:9 NMC:CB:lignin cathodes provided proper cohesion forces between the coated particles (i.e., a high electronic conductivity). The calendering; therefore, seemed to limit the ionic conduction pathways for the Li⁺ by removing pores, without improving the electrical conductivity. We conclude that the large CB/lignin-matrix already created a sufficient electronic conductivity for the uncalendered low mass loading (7.4 mg/cm²) cathodes and that the low thickness (< 76 μm) provided an effective Li⁺-diffusion path. Thus, the calendering sacrificed the Li⁺-diffusion network by decreasing the porosity without improving the electrical conductivity, and consequently, the rate capability decreased.

However, the opposite trend was detected for the lignin/water cathodes with higher mass loading (9.7 mg/cm²). When increasing the mass loading, and thus the cathode thickness to (> 76 μm), the calendering likely improved the ionic conductivity by decreasing the thickness.

Thus, calendering lignin cathodes with a certain high thickness (> 76 μm) improved the ionic and electronic conductivity, whereas calendering cathodes with a low thickness (< 76 μm) reduced the ionic pathways without improving the electronic network.

Interestingly, the PVDF/NMP-fabricated cathodes of similar mass loading (6.6±0.6 (Al) and 6.1±0.8 (C-Al) mg/cm²) in Figure S9a also showed the opposite trend to the 7.4 mg/cm² lignin/water-based cathodes. The rate capability increased with lower porosities (30 %). This was in agreement with other studies on PVDF/NMP-based cathodes, which reported that calendering down to a porosity of 30 - 40 % was necessary to provide an optimal electronic conductivity⁵³. The need for a lower porosity indicated that the CB/binder-network within the 85:10:5 PVDF-based coating provided poor electrical conductivity compared with the 80:11:9 lignin-based cathodes.

It was; however, difficult to distinguish to what extent the improved electrical conductivity for the lignin-based cathodes was attributed to 1) the higher electrical conductivity of lignin relative to the PVDF, or 2) the higher amount of inactive material (CB and lignin) which provided more connection points to the active NMC111 particles in the 80:11:9 lignin/water-cathodes compared with the 85:10:5 PVDF/NMP-cathodes⁵¹.

An important factor to contemplate when comparing the rate capability of lignin/water-based cathodes to PVDF/NMP-based cathodes, is the additional LiOH and Li₂CO₃ surface layer formed when the NMC111 particles are exposed to water. This phenomena will be further discussed in subsection 3.7.2.

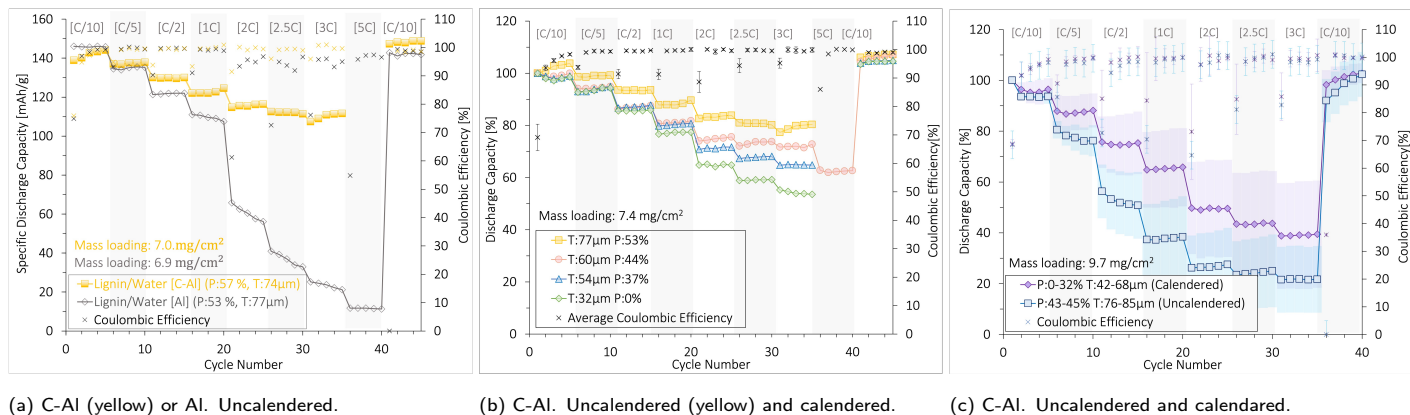


Fig. 10 The rate capability (%) and coulombic efficiency (%) of uncalendered and calendered lignin/water-based NMC111 cathodes with (a), (b) low and (c) high mass loading, resulting in different thicknesses (T) and porosities (P). An SEM analysis of the cathode surfaces in (b) is presented in Figure 7. The cathodes were cycled at different [C-rates] (1 C = 160 mA/g) in coin cells at 22 °C between 3.0 - 4.3 V (vs Li^+/Li) using a Li-metal anode. The plots with deviation bars show the average and of three cells deviation of three cells.

To conclude, the relationship between ionic and electronic conductivity within the different cathode coatings explained why the capacity decreased under high calendering pressures for lignin/water-based cathodes with large carbon matrix (20 %) in Figure 10b, while the opposite trend was observed for the lignin/water-based cathodes of high mass loading in Figure 10c and the PVDF-based cathodes with similar mass loading (6.1-7.2 mg/cm^2) but lower carbon content (10 wt %) in Figure S9a.

Additionally, the low rate capability at high calendering pressure (P_{high} : 40 - 45 μm gap) for the lignin/water-cathodes of low mass loading (7.4 mg/cm^2) may to some extent be explained by the NMC111 particle crushing found in cathodes with $\sim 0\%$ porosities (Figure 7), or a Li^+ -transport pore-blocking effect formed when calendering cathodes with a large carbon-based matrix (80 wt % NMC111).

Kang *et al.*⁷⁰ found that crushed NMC111 particles decreased the rate capability as many loosely connected NMC111 particles became inactive at high C-rates.

Zheng *et al.*⁵³ and Rollag *et al.*⁹ reported that NMC111 cathodes with extremely low porosities ($\sim 0\%$) suffered from a high activation barrier for Li^+ -transfer at the electrode/electrolyte interphase which reduced the cathode's rate capability. Haselrieder *et al.*⁷¹ reported such an activation barrier on the surface of anodes may introduce poor electrolyte penetration and problems associated with the electrolyte wetting. However, also reported that the Li^+ -transfer was closely associated with the fraction of inactive material (carbon black and lignin) rather than with the degree of calendering pressure (i.e., porosity)⁵³.

In the next section, the lignin/water-based cathodes with a large (80:11:9) and small (90:5:5) carbon/lignin-matrix

are compared to understand how the carbon/lignin-matrix influenced the electrolyte wettability. The porosity was kept constant ($\sim 45\text{-}50\%$).

3.6.2 Electrolyte Wetting

A three-electrode PAT cell was used to separate the capacity responses from the lignin/water-based 80:11:9 cathode and the Li-metal anode and is presented in Figure 11. The potential plateau indicating Li^+ -(de)intercalation was initially short but extended over multiple cycles. This feature was assigned to the cathode since the cathode's capacity curve featured the same response as the total cell (E_{cell}). The poor wetting of the cathode prevented the pores in the cathode coating from filling with the electrolyte which hindered Li^+ -(de)intercalation and activation of the NMC111 close to the Al-foil. This resulted in a low cell capacity during the first cycles.

The poor wetting behavior became apparent when comparing the soaking time of a 10 μL drop of electrolyte on a lignin-based 80:11:9 and PVDF-based 90:5:5 cathode. The former showed >12 times slower wetting (Figure S1b).

To understand the influence of the wetting and CB/lignin-matrix on the long-term cyclability, lignin/water-cathodes with 80:11:9 and 90:5:5 wt % NMC111:CB:lignin were soaked in the electrolyte for 1, 3, 6, or 35 day(s) before being cycled. The corresponding discharge capacities and coulombic efficiencies are shown in Figure 12.

Both Figure 12a and Figure 12b showed a decreasing initial discharge capacity (at C/10) and capacity retention (after 100 cycles at C/2) with shorter electrolyte wetting times for the lignin/water-cathodes. When the electrolyte exposure time was short, the cathodes with an 80:11:9 ratio in Figure 12a showed a decreasing capacity in the first ~ 25



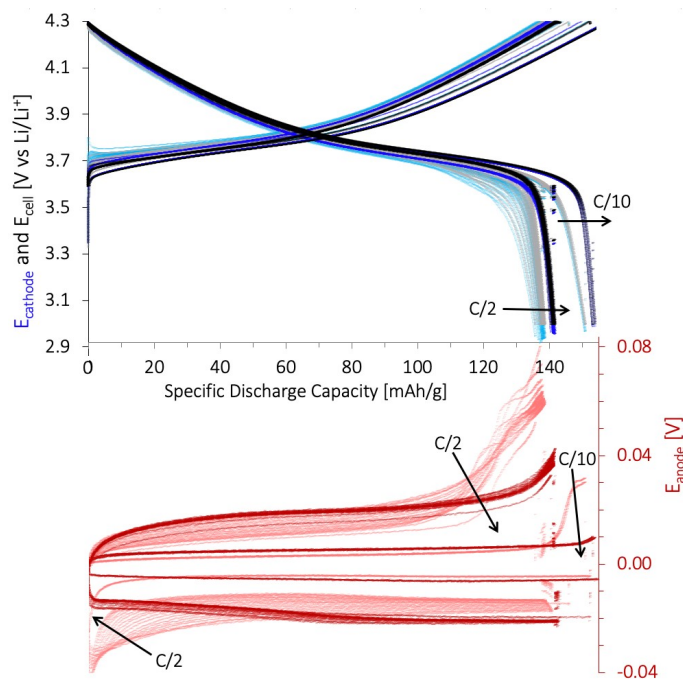


Fig. 11 The galvanostatic cycling performance of a PAT cell using Li metal as anode and reference electrode. The response from the Li-metal anode (red E_{anode}), NMC111 working cathode (blue E_{cathode}), and both (black E_{cell}) were measured. The lignin/water-cathode (80:11:9 wt % NMC111:CB:lignin) was coated on C-Al-foil, with 7.4 mg/cm^2 mass loading and calendered at P_{medium} . The cell was cycled after a 8 days wetting period for 5 cycles at C/10, 21 cycles at C/2 (light colour), 5 cycles at C/10, and 21 cycles at C/2 (dark colour) between 3.0 - 4.3 V vs Li^+/Li (1 C = 160 mA/g) at 22°C . Arrows represent an increasing cycle number. The cathode surface area used for PAT cells was larger (2.54 cm^2) compared to the coin cells (1.78 cm^2) and the separator was glass fiber.

cycles. The capacity drop gradually became less prominent by increasing the electrolyte wetting time from 1 to 6 days before cycling the cell. This phenomenon is also often recognized in silica-based anodes as poor electrolyte wetting³⁷. Thus, we believe that a poor electrolyte penetration into the cathode explained the declining capacity detected for lignin/water-based 80:11:9 cathodes during the first ~ 25 cycles.

When reducing the CB and lignin wt % to about half (90:5:5 wt % NMC111:CB:lignin), the wetting process improved as shown in Figure 12b. A 90:5:5 cathode soaked for 35 days in the electrolyte before cycling (red) obtained similar electrochemical performance over 100 cycles as the PVDF/NMP-based baseline cathode (blue).

On the other hand, when cycling such lignin/water-based 90:5:5 cathodes after being soaked in electrolyte for 1 day (pink), the capacity decrease caused by wetting was less apparent than for those with a high matrix, but the

capacity decreased rapidly over the next 100 cycles. The CE was also unstable, suggesting that cracking and loss of active material occurred.

Although wetting was improved by reducing the CB/lignin matrix to 10 %, the insufficient soaking of the cathode may cause local differences in the CEI layer formation and non-uniform stress accumulation in the cathode material, as volume expansion and contraction take place in the NMC111 particles during cycling. A large amount of NMC111 (90 %) in combination with a small CB/lignin matrix did not seem to provide sufficient mechanical strength to sustain these stresses during cycling. This provoked crack propagation, and loss of active material, and eventuated in a rapid capacity fade for the 90:5:5 cathodes wetted for 1 day.

To conclude, the short voltage plateau during the first cycles in Figure 11 was attributed to poor cathode wetting. Lu *et al.*²² reported the same reduction of the voltage plateau and a lower discharge capacity when applying lignin as binder material. They did not detect such a trend for the uncalendered lignin-cathodes, and wettability is known to decrease with pore removal by calendering³⁷.

This phenomenon explains why there is a dip during the first 5 formation cycles for the calendered lignin/water-based cathodes in the rate capability plot in Figure 10. In contrast, no such dip was seen for the uncalendered cathodes with proper wetting. Thus, the poor electrolyte wettability of the 80:11:9 lignin/water cathodes can be improved by either increasing the porosity or reducing the CB/lignin-matrix from 20 to 10 wt %.

Problems related to wetting are common for other electrode chemistries, and other methods have been assessed to increase the wetting rate^{37,72}. Al-Shroofy *et al.*⁴⁶ reported that wetting abilities decreased for calendered PVDF/NMP-cathodes as pores usually increase the electrolyte uptake. Sheng *et al.*¹⁵ utilized additives and different electrolytes to improve the electrode's electrolyte-wettability. Pfeeding and Pröll³⁶ observed a dramatic acceleration of electrode wetting by utilizing a set of laser-induced micro-channels with a width of $40 - 55 \mu\text{m}$ (NMC111 cathode) and $70 \mu\text{m}$ (LMO cathode).

3.7 Water Exposed NMC111

No significant difference was detected in the initial capacity at low C-rates (C/10) when comparing the aqueous processed NMC111 cathodes to those fabricated with PVDF/NMP (Table 2). However, there was a larger capacity loss at higher C-rates (C/2-5C) and after long-term cycling (100 cycles) at C/2 for the lignin/water cathodes compared to the NMP/PVDF cathodes. This was not necessarily



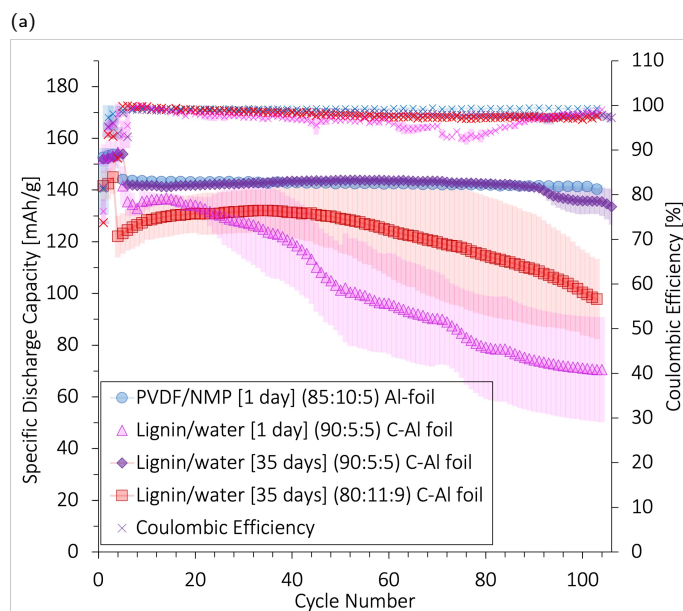
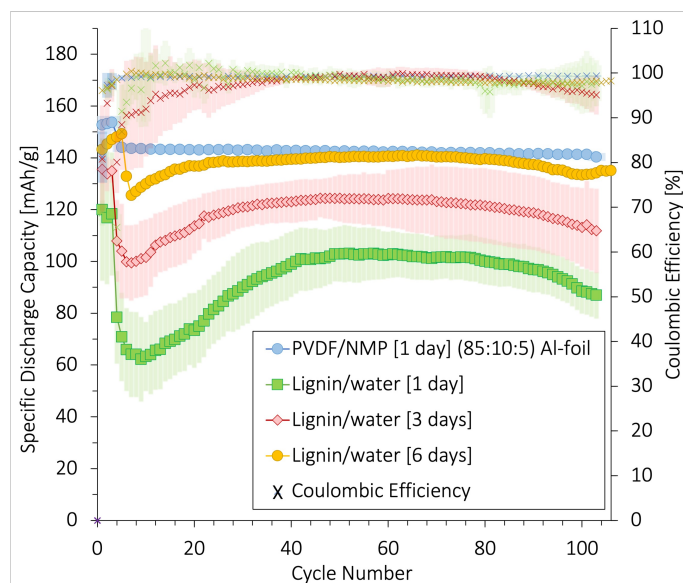


Fig. 12 The average specific discharge capacity (mAh/g) and coulombic efficiency (%) of three coin cells and their standard deviation. The lignin/water cathodes were coated onto a C-Al current collector with 80:11:9 wt % NMC111:CB:binder unless specified. The days refer to The mass loading for all cathodes was $7.4 \pm 0.3 \text{ mg/cm}^2$. An 85:10:5 PVDF/NMP-based cathode with comparable mass loading ($6.6 \pm 0.6 \text{ mg/cm}^2$) coated onto a plain Al-foil and wetted for 1 day (blue circles) was used as the baseline. The cathodes were cycled in coin cells between 3.0 - 4.3 V (vs Li⁺/Li) using a Li-metal anode. The C-rate was C/10 for the first 3 or 5 cycles and C/2 for the following 100 cycles.

caused by the lignin binder, but rather the water solvent. In this section, we discuss the formation of restive Li₂CO₃ and LiOH surface layers on NMC111 during the aqueous slurry production, HF-formation during cycling, and the corrosion

of the Al-foil.

3.7.1 LiOH and Li₂CO₃ surface formation

Firstly, a slight formation of LiOH and Li₂CO₃ surface layers were confirmed by XRD and XPS measurements conducted on pristine, humidity-exposed, and water-exposed NMC111 particles (Figure S15 and Figure S17). The penetration of the XPS signals implied that the formation of Li₂CO₃ and LiOH surface layers upon humidity and water exposure was negligible and thin (>2-5 nm) compared to early reports (10 nm)⁴⁵. This was in accordance with Jung *et al.*⁴³ which calculated the Li₂CO₃-layer to be 1.2-1.4 nm thick for pristine and NMC111 particles stored in air for 1 year. This was likely the equilibrium surface layer formed after the production of the NMC111. A more comprehensive elaboration on the XPS measurements is found in subsection 5.3.3.

XRD profiles in Figure S15 confirmed that no major change in the bulk crystallinity nor the appearance of secondary phases were observed for the water- and humidity-exposed NMC111 particles. A Rietveld refinement of the XRD spectra (Table S3) showed a slight reduction in the unit cell volume for the NMC111 after being exposed to water (-0.011 %) and air (-0.015 %). Such a trend was reported earlier for NMC111 particles exposed to acid to be a sign of Li⁺-leaching from the surface of NMC111⁷³, although those values were > 40 times higher.

Furthermore, XRD spectra may be used to determine the degree of Ni²⁺/Li⁺ cation mixing in the NMC111 particles. Cation mixing occurs when Ni²⁺ of similar radius as Li⁺ migrate from the octahedral 3b transition metal-(TM)-sites to the octahedral 3a Li⁺-sites. If the charge compensation of the lost Li⁺ during water exposure promotes the reduction of Ni³⁺ to Ni²⁺ and the migration of surface Ni²⁺ into the Li⁺-depleted layer, the XRD Rietveld refinement is expected to show a higher Li⁺/Ni²⁺ cation mixing in water- and humidity-exposed NMC111 particles^{29,43,74}.

No such increase was observed from the Rietveld refinement (Table S3) and the degree of cation mixing remained low for NMC111 particles regardless of storage conditions or solvent exposure (<1.99 % Ni²⁺ in the Li⁺-layers). In fact, the cation mixing decreased relative to the pristine NMC111⁷⁴. Thus, few migrating Ni²⁺ species were likely present, and there was no sign of Ni³⁺ reduction upon water exposure. These findings supported the conclusion drawn from the XPS measurements in Figure S17, which showed no change in the Ni 2p peak for humidity- or water-exposed particles. Thus, we conclude that the charge compensation of Li⁺ during Li⁺-leaching of the water- and humidity-exposed NMC111 particles were mainly H⁺-exchange rather than the reduction of Ni³⁺ to



Ni²⁺²⁹.

It should be mentioned that the cation mixing is generally more prominent in Ni-rich NMC materials (NMC811), as the ratio between Ni³⁺/Ni²⁺ is higher⁷⁴. There are more Ni³⁺ available for reduction, which explains why an increase in cation mixing was detected in the XRD scans for water-exposed Ni-rich NMC in earlier reports⁷⁴, and not for NMC111 particles²⁹.

3.7.2 The Electrochemical Performance

There is some disagreement in the literature as to what extent the electrochemical performance is affected by the Li⁺-leaching and the Li₂CO₃ and LiOH surface layers when NMC111 particles are exposed to humidity and water.

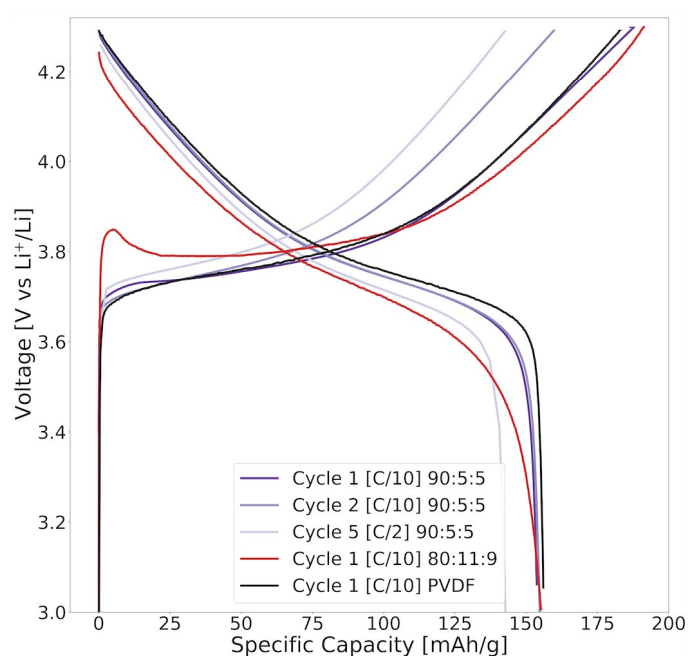


Fig. 13 The voltage profile of the first and second cycle at C/10 and the fifth cycle at C/2 for NMC111 cathodes fabricated using 80:11:9 (red) or 90:5:5 (purple) lignin/water (7.4 mg/cm²), and 85:10:5 PVDF/NMP-fabricated cathodes (black) (6.9 mg/cm²). The cathodes were cycled in coin cells between 3.0 - 4.3 V (vs Li⁺/Li) at different [C-rates] at 22°C using a Li metal anode. 1C = 160 mA/g.

Firstly, the electrodes were dried at 120 °C under vacuum to remove all moisture before cell assembly. The voltage profiles of the water-based NMC111 cathodes assembled in half-cells showed a delithiation voltage peak at the beginning of the first charge Figure 13. This initial potential peak completely disappeared from the profile in the subsequent cycles (Figure S11 and was not present for the NMP/PVDF-based cathodes. It is generally attributed to the dissolution of the insulating species formed at a humidity-exposed NMC particle surface, and usually in-

creases with thicker LiOH and Li₂CO₃-layers for Ni-rich electrodes⁴³. This surface impurity act as a resistive film around the NMC111 particles, and must be partially decomposed before delithiation can occur⁴³. Since it decreases for 90:5:5 cells, it indicates that the higher lignin content promoted this peak. We believe that there is a surface layer on the NMC particles in the lignin cathodes that dissolve upon delithiation, which may be a combination of LiOH or Li₂CO₃ from the water-NMC111 reaction and NaOH or N₂S residuals deposited from the lignin-binder.

Studies report an absence of such a peak during the first charge of full cells^{29,43}, implying that such decomposition reaction occurs between the insulating surface compounds and the Li metal anode, rather than at the cathode. However, it should be mentioned that in the case of a graphite anode, the reactive surface area increases, and the compounds formed on the water-based cathode can be diluted at the graphite surface²⁹.

At a low rate of C/10, the lignin/water-based cathodes did not face any significant loss in capacity due to the water treatment of NMC111 Figure 13. Most studies report little to no difference in the capacity at low C-rates (< C/2) when comparing water-exposed NMC111 cathodes with those exposed to NMP^{41,64,74}. According to Memm *et al.*⁶⁴ only 0.63 % of Li⁺ per formula unit Li_{1.034}Co_{0.33}Mn_{0.33}Ni_{0.33}O₂ were lost from the NMC111 surface due to Li⁺/H⁺ exchange, and were considered negligible for the performance^{41,64,74,75}.

Such small Li⁺-depletion in the NMC111 surface was negligible for the capacity and was likely compensated for already in the first charge cycle as the cells were cycled in excess Li⁺ using a Li metal anode. However, since we assume that the main charge compensation for the Li⁺-leaching in the surface layer of the NMC111 lattice was H⁺/Li⁺-exchange, the H⁺ may react with fluorine (F) in the electrolyte and form HF during cycling. This reaction directly dissolves the metal ions in the cathode lattice leading to gas evolution, and phase transformation from the layered to spinel at the charged state³⁴. This reaction is therefore known to be detrimental to the battery capacity upon subsequent cycles and is likely causing more damage to these half-cells rather than the loss of Li⁺⁷⁶.

It should; however, be mentioned that the charge capacity is highest for the lignin/water cathodes relative to the PVDF/NMP cathodes. The additional charge capacity in the first cycle (at high voltages >4.2 V) could potentially be attributed to the large oxidation current peak provided by lignin in the CV scan (Figure 4b). Both features disappeared upon cycles indicating that these were irreversible depletion reactions.

When increasing the C-rate to C/2 in Figure 13, there



was a more prominent capacity loss for the lignin/water-based NMC111 cathodes compared with the PVDF/NMP-based cathodes with similar mass loading. There was also a higher polarization for the water-exposed NMC111 cathode indicating a higher resistance, which can be caused by the poor wetting of the lignin binder, the oxidation of the binder, or the presence of alkali residuals. This was in agreement with other studies looking at cathodes with water- or humidity-exposed NMC111 particles^{16,41,45,74}. Looking at the subsequent cycles with the same C-rate (Cycle 10 and 15 in Figure S10b), the polarization decreased.

Most studies agree that the Li⁺-diffusion limitation restricts the (de)intercalation of Li⁺ and is the main reason for a larger capacity loss at high C-rates when comparing water- and NMP-exposed NMC111 particles. However, the mechanism behind the Li⁺-diffusion limitation varies across scientific articles.

Azhari *et al.*⁷⁴ reported that the LiOH and Li₂CO₃ surface layers increased the surface resistance on the NMC111 particles, which kinetically limited the intercalation. Meanwhile, Wood *et al.*⁴¹ reported that the lower rate capability for water-exposed NMC811 particles was caused by the different slurry fabrication procedure, as SEM images revealed more binder coverage on water-processed NMC particles compared with NMP-fabricated NMC particles. A higher coverage ultimately increased the Li⁺-diffusion resistance.

In this article, no additional Li₂CO₃ and LiOH residuals were found. The different binder compositions, slurry mixture procedures, and coverage of NMC111 particles made it hard to distinguish whether the capacity loss at high C-rates for aqueous processed cathodes was caused by the Na₂S and NaOH residuals formed upon water exposure or other fabrication parameters⁴¹.

When looking at the capacity loss over multiple cycles, studies generally conclude that cathodes made of water-exposed NMC111 particles deteriorate more rapidly during cycling compared to pristine particles. For example, Azhari *et al.*⁷⁴ reported a capacity fade of 69 % over 100 cycles at C/2 for water exposed NMC111 cathodes.

Even the best performing lignin/water-cathodes (lignin/water, 90:5:5, 35 days) obtained a slightly worse cyclability (100 cycles) than the PVDF/NMP-cathodes. This capacity deterioration over multiple cycles is likely explained by the water exposure of NMC111 particles and is caused by a series of phenomena; including the partial isolation of active NMC111 material,^{45,74} growth of a restive surface layer⁷⁴, and reaction between the electrolyte and H⁺ residuals to form hydrofluoric acid (HF)^{69,76}. These degradation reactions usually get progressively larger for Ni-rich cathodes NMC811 cathodes with a more prominent

LiOH and Li₂CO₃ surface layers^{41,43}.

3.7.3 pH measurements

pH measurements were conducted during the mixing of NMC111 particles into pure water solvent and during the slurry fabrication of a lignin/water-based slurry with the (80:11:9):1.7 (NMC111:CB:lignin):solvent ratio. The measurements are presented in Figure 14, and at the initial pH, no NMC111 particles were present. The CB and lignin were already mixed with the water for the slurry mixtures. No pH increase was detected when adding the CB and the NMC111 was the main species contributing to the measured pH increase presented in Figure 14.

Figure 14 shows that when exposing NMC111 particles to water, the pH drastically changed during the first minute. Wood *et al.*⁴¹ reported a similar increase in the initial pH and long-term pH values for the NMC111 particles as shown in Figure 14. The increase was caused by Li⁺-leaching from the NMC111 surface and originated from a combination of dissolution of LiOH and Li₂CO₃ surface species from the NMC111⁴¹, following the mechanism presented in Figure 2.

The lignin/water-based slurry showed a high initial pH of 9.5. This was caused when dissolving lignin in water, as the pH increased from ~6 to 9.5. The pre-mixed lignin/water (1:10 wt %) solution used for slurry fabrication had a high initial pH (9.4). Such high initial pH for the lignin/water-slurry in Figure 14 was caused by the dissolution of kraft lignin in water. Kraft lignin is extracted from the oil using an alkali process, and alkali residuals (such as NaOH or Na₂S) are often left on the lignin if a neutralization process does not take place after the extraction. During the dissolution of lignin in water, these alkali residuals increased the pH from 5.8 to 9.4. Lignin is usually insoluble in water but becomes soluble if dissociation of its phenolic hydroxy group in Figure 1 occurs¹⁷. At pH 9.4, the phenolic hydroxy group was activated by the removal of its H⁺ which enabled the dissolution of lignin in water. The alkali species were; therefore, necessary to dissolve the lignin and make a homogeneous dispersion, and eventually a homogeneous cast. The phenolic hydroxy groups have a pK_a around 10, meaning at the pH of 9.4, nearly all phenolic hydroxy groups were activated.

After the initial increase in pH to 9.4, the pH increased to 10.4 after the first minute, before stabilizing at 10.5 after a day. In Figure 14, such a small increase may indicate that the initial increase in pH caused by dissolving lignin in water suppressed the Li⁺/H⁺-exchange that occurs when NMC111 is introduced to water. However, the characteristic overpotential increase at the beginning of the first charge curve in Figure S10b indicated that the Li residuals



were still present on the NMC111 particle surface. Wood *et al.*⁴¹ also reported that the Li⁺ leaching took place in basic solutions (pH 12) as well as acidic solutions (pH 2). The high initial pH caused by adding lignin likely camouflaged the pH rise associated with Li⁺-leaching from the NMC111. After 24 hours, twice the amount of water was added to the lignin/water-slurry mix (points marked X in Figure 14). The pH remained stable, indicating that the Li⁺-leaching had reached a saturation point⁴¹.

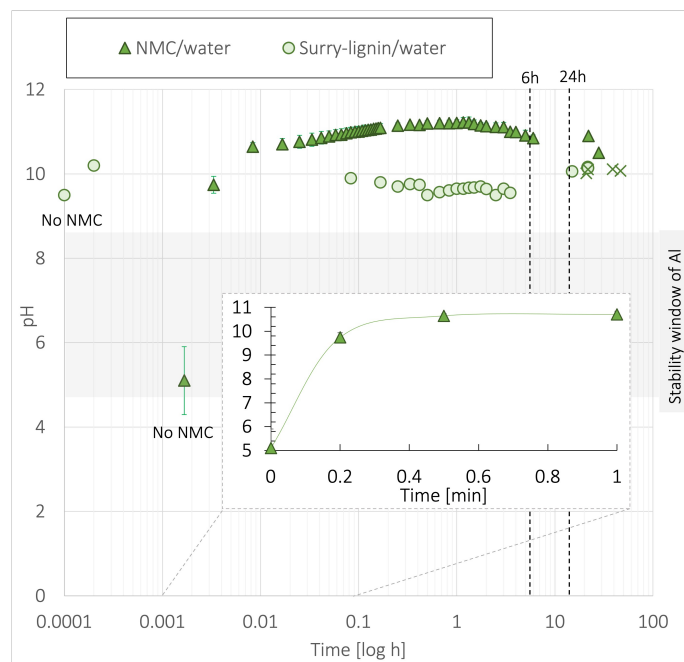


Fig. 14 The pH measurement during the mixture of water with a low concentration of NMC111 powder (11.45 wt%) or as a slurry ((NMC111:CB:lignin):water) with a high NMC111 concentration ((80:11:9):1.7) at 22 °C. The point measurements display the average of two measurements. The points denoted "x" are measurements taken after adding extra water to the lignin/water slurry.

Since the maximum content of lignin in any lignin/water-cathode was 9 wt %, only a trace amount of the alkali species were assumed to be present in the lignin/water-based 80:11:9 cathodes. EDS scans in Supplementary Table S2 reveal that sodium (Na) (2.72 ± 0.84 wt %) and sulphur (S) residuals (0.35 ± 0.18 wt %) were present in the uncycled lignin/water-cathodes, and their presence decreased to 0.28 ± 0.02 and 0.25 ± 0.04 after 54 cycles, respectively. These species were not found in the PVDF/NMP-based cathode's EDS and XRD spectra in Figure S8 and Figure S16a, respectively. An additional XRD scan of the lignin raw material confirmed their origin (Figure S16b).

The cycling curve generally obtained the typical NMC111 shape, and no apparent signs of the S and Na species were observed in the cycling curves. However, the

impact of these species on the electrochemical performance should be further investigated before the commercialization of kraft lignin as a binder material. Interestingly, Na is often used as an additive in Na-CMC binders^{3,16,77–79}, and its presence is not considered harmful to the battery. S was present in such a small amount and was neglected in this study.

The corrosion of the Al can be avoided by using acids such as phosphoric acid (PA) as an additive; however, a high pH was needed for lignin to dissolve in water. Furthermore, the NaOH in the slurry during lignin/water-slurry fabrication may undergo neutralization reactions with the PA additive to form Na_3PO_4 , and a protective carbon-coated Al-foil (C-Al-foil) was, therefore, the focus of this paper. An additional study on the use of PA as a pH controller during slurry fabrication and the use of a PA coating to eliminate the surface residuals (LiOH and Li_2CO_3) can be found in subsection 5.4.

4 Conclusion

Cyclic voltammetry (CV) revealed that lignin undergoes an oxidation reaction during the first cycle with the electrolyte between 2.8 - 4.5 V, but stabilized over multiple cycles. Irreversible oxidation reactions contributed to an overall higher charge capacity and lower average coulombic efficiency over 100 cycles for lignin/water-cathodes (98.2 %) compared with PVDF/NMP cathodes (99.2 %). Differential scanning calorimetry (DSC) reveals that lignin was thermally stable at temperatures up to 152 °C. When replacing the PVDF/NMP with lignin/water during slurry fabrication, rheology measurements revealed that a lower liquid content was needed to obtain the same optimal viscosity for tape casting.

When gradually replacing the PVDF/NMP with lignin/NMP, the lignin accumulated at the surface at high evaporation rates (90 °C), the adhesion to Al decreased, and the initial specific discharge capacity dropped. By decreasing the drying temperature to 50 °C, a more controlled NMP evaporation occurred, the accumulation of lignin at the cathode surface diminished, and its mechanical strength and specific capacity increased accordingly. By replacing the NMP solvent with water, the accumulated surface layer of lignin diminished and the capacity increased. The high surface tension of water relative to NMP caused a higher capillary pressure in the vacuum drying processes of aqueous slurries, which led to extensive cracking in the coating at 90 °C. Electrode drying at 50 °C and calendaring reduced surface cracks. The calendaring magnified the nature of the initial mechanical strength, intensifying a poor adhesion of the coating to the Al-foil and strong cohesion between particles. Pen and



scratch tests confirmed that the lignin binder provided strong cohesion forces to carbon black. By replacing the Al current collector with a carbon-coated Al current collector (C-Al), the aqueous processed lignin-based NMC111 cathodes obtained mechanical stability compared to the PVDF/NMP baseline cathodes.

Calendering cathodes with a large binder matrix decreased the thickness and porosity, induced pore blocking, and created a barrier for Li⁺-transport, which eventually lowered the rate capability. While calendering and pore removal improved the rate capability for PVDF/NMP-based cathodes, the rate capability of lignin/water-based cathodes decreased with lower porosity and higher mass loading (9.7 mg/cm²).

The NMC111 cathode using pure lignin as a binder, coated onto a carbon-coated Al (C-Al) current collector, dried at 50 °C, with a mass loading of 7.4 mg/cm² obtained 63 % capacity retention at 5 C. The cathodes using a CMC/lignin binder and a mass loading of 5.1-5.6 mg/cm² obtained 60 % capacity retention at 5 C, independent of the current collector (Al or C-Al).

The aqueous-produced NMC111 cathodes with lignin binder obtained poor electrolyte wetting compatibility with the organic 1 M LiPF₆ in EC/DMC/DEC electrolyte. The cycling performance of the lignin-based cathodes improved with longer electrolyte wetting exposure before cycling, additional formation cycles at C/10, higher porosity, and a smaller CB/lignin matrix. Consequently, the 90:5:5 wt % lignin/water-cathodes wetted for 35 days with 5 formation cycles at C/10 showed similar initial discharge capacity and capacity retention (154 mAh/g and 89 %) as to 85:10:5 PVDF/NMP-cathodes (153 mAh/g and 93 %) after 100 cycles at C/2.

During the first charge cycle, lignin underwent an oxidation reaction that diminished over subsequent cycling. This caused a large charge capacity detected in the voltage curve during the first galvanostatic cycle. This current contribution was almost undetectable in the second cycle and diminished over multiple cycles.

The electrochemical, thermal, and mechanical stability of lignin suggests high applicability to other high Ni-containing NMC cathodes. Since the aqueous production of CMC-based NMC811 cathodes with minimal Li⁺ leaching has been reported⁴¹, the electrolyte wettability of lignin needs to be improved before its commercialization as a binder.

The pH measurements and XRD confirmed the presence of Li⁺-leaching from the NMC111 particle surface during water exposure and slurry fabrication. The aqueous processing of NMC111 cathodes did not decrease the initial capacity of the cells at a low rate (C/10) but decreased the

rate capability and long-term cyclability at higher C-rates.

Author Contributions

O.S.B.: Writing – review and editing, Supervision, Conceptualization, Project administration, Funding acquisition. A.M.S.: Writing – review and editing, Supervision, Validation. J.J.L.: Writing – review and editing, Supervision, Validation. P.R.S.: Writing – review and editing, Supervision, Validation. I.T.: Data curation, Formal Analysis. S.N.B: Methodology, Investigation, Data curation, Formal Analysis, Conceptualization, Writing – original draft.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors would like to acknowledge financial support from FREYR (Project number: 90492502), ENERSENCE, and InnoEnergy. Our gratitude is extended to the Department of Materials Science and Engineering, NTNU, as the XPS measurement and data analysis were conducted by Dr. Verner Håkonsen and Dr. Mahsa Ebadi. Further, we thank BSc. Nora Kvalsvik for the pH measurements and the graphic illustration of Li⁺-leaching.



Notes and references

- 1 S. D. Kurland, *Environmental Research Communications*, 2020, **2**, 012001.
- 2 L. A.-W. Ellingsen, B. Singh and A. H. Strømman, *Environmental Research Letters*, 2016, **11**, 1–9.
- 3 S. N. Bryntesen, A. H. Strømman, I. Tolstorebrov, P. R. Shearing, J. J. Lamb and O. Stokke Burheim, *Energies* 2021, Vol. 14, Page 1406, 2021, **14**, 1406.
- 4 D. L. Wood, J. D. Quass, J. Li, S. Ahmed, D. Ventola and C. Daniel, *Drying Technology*, 2018, **36**, 234–244.
- 5 D. L. Wood, J. Li and C. Daniel, *Journal of Power Sources*, 2015, 234–242.
- 6 J. Li, Y. Lu, T. Yang, D. Ge, D. L. Wood and Z. Li, *iScience*, 2020, **23**, 101081.
- 7 Y. Li, *IOP Conference Series: Earth and Environmental Science*, 2020, **514**, 042019.
- 8 I. Doberdò, N. Löffler, N. Laszczynski, D. Cericola, N. Penazzi, S. Bodoardo, G. T. Kim and S. Passerini, *Journal of Power Sources*, 2014, **248**, 1000–1006.
- 9 K. Rollag, D. Juarez-Robles, Z. Du, D. L. Wood and P. P. Mukherjee, *ACS Applied Energy Materials*, 2019, 4464–4476.
- 10 T. C. Nirmale, B. B. Kale and A. J. Varma, *A review on cellulose and lignin based binders and electrodes: Small steps towards a sustainable lithium ion battery*, 2017.
- 11 R. Sahore, M. Wood, A. Kukay, Z. Du, K. M. Livingston, D. L. Wood and J. Li, *Journal of The Electrochemical Society*, 2022, **169**, 040567.
- 12 S.-L. Chou, Y. Pan, J.-Z. Wang, H.-K. Liu and S.-X. Dou, *Phys. Chem. Chem. Phys.*, 2014, **16**, 20347.
- 13 D. Bresser, D. Buchholz, A. Moretti, A. Varzi and S. Passerini, *Energy and Environmental Science*, 2018, **11**, 3096–3127.
- 14 Y. Ma, J. Ma and G. Cui, *Energy Storage Mater.*, 2019, **20**, 146.
- 15 Y. Sheng, *Theses and Dissertations*, 2015, 1–146.
- 16 F. A. Çetinel and W. Bauer, *Bulletin of Materials Science*, 2014, **37**, 1685–1690.
- 17 M. Ragnar, C. T. Lindgren and N.-O. Nilvebrant, *Journal of Wood Chemistry and Technology*, 2000, **20**, 277–305.
- 18 F. S. Chakar and A. J. Ragauskas, *Industrial Crops and Products*, 2004, **20**, 131–141.
- 19 V. K. Thakur, M. K. Thakur, P. Raghavan and M. R. Kessler, *ACS Sustainable Chemistry and Engineering*, 2014, **2**, 1072–1092.
- 20 W. Li, Y. Zhang, L. Das, Y. Wang, M. Li, N. Wanninayake, Y. Pu, D. Y. Kim, Y. T. Cheng, A. J. Ragauskas and J. Shi, *RSC Advances*, 2018, **8**, 38721–38732.
- 21 S. D. Gong, Y. Huang, H. J. Cao, Y. H. Lin, Y. Li, S. H. Tang, M. S. Wang and X. Li, *Journal of Power Sources*, 2016, **307**, 624–633.
- 22 H. Lu, A. Cornell, F. Alvarado, M. Behm, S. Leijonmarck, J. Li, P. Tomani and G. Lindbergh, *Materials*, 2016, **9**, 127.
- 23 V. Ponnuchamy and E. S. Esakkimuthu, *Applied Surface Science*, 2022, **573**, 151461.
- 24 W. E. Tenhaeff, O. Rios, K. More and M. A. McGuire, *Advanced Functional Materials*, 2014, **24**, 86–94.
- 25 D. Jeong, J. Shim, H. Shin and J. C. Lee, *ChemSusChem*, 2020, **13**, 2642–2649.
- 26 D. Kai, M. J. Tan, P. L. Chee, Y. K. Chua, Y. L. Yap and X. J. Loh, *Green Chemistry*, 2016, **18**, 1175–1200.
- 27 W. O. Doherty, P. Mousavioun and C. M. Fellows, *Industrial Crops and Products*, 2011, **33**, 259–276.
- 28 Z. Du, K. M. Rollag, J. Li, S. J. An, M. Wood, Y. Sheng, P. P. Mukherjee, C. Daniel and D. L. Wood, *Journal of Power Sources*, 2017, 200–206.
- 29 M. Bichon, D. Sotta, N. Dupré, E. De Vito, A. Boulineau, W. Porcher and B. Lestriez, *ACS Applied Materials and Interfaces*, 2019, **11**, 18331–18341.
- 30 W. Man and W. B. Russel, *Physical Review Letters*, 2008, **100**, 198302.
- 31 H. Zheng, J. Li, X. Song, G. Liu and V. S. Battaglia, *Electrochimica Acta*, 2012, **71**, 258–265.
- 32 F. Buss, C. C. Roberts, K. S. Crawford, K. Peters and L. F. Francis, *Journal of Colloid and Interface Science*, 2011, **359**, 112–120.
- 33 M. Stein, A. Mistry and P. P. Mukherjee, *Journal of the Electrochemical Society*, 2017, **164**, A1616–A1627.
- 34 C. Busà, M. Belekoukia and M. J. Loveridge, *Electrochimica Acta*, 2021, **366**, 137358.
- 35 P. Li, Y. Zhao, Y. Shen and S.-H. Bo, *Journal of Physics: Energy*, 2020, **2**, 022002.
- 36 W. Pflöging and J. Pröll, *Journal of Materials Chemistry A*, 2014, **2**, 14918–14926.
- 37 A. Davoodabadi, J. Li, H. Zhou, D. L. Wood, T. J. Singler and C. Jin, *Journal of Energy Storage*, 2019, **26**, 101034.
- 38 H. Berg, *Batteries for electric vehicles : Materials and Electrochemistry*, Cambridge University Press, 2015, pp. 1–250.
- 39 J. Xiao, Q. Li, Y. Bi, M. Cai, B. Dunn, T. Glossmann, J. Liu, T. Osaka, R. Sugiura, B. Wu, J. Yang, J. G. Zhang and M. S. Whittingham, *Nature Energy* 2020 5:8, 2020, **5**, 561–568.
- 40 A. Tornheim and D. C. O'Hanlon, *Journal of The Electrochemical Society*, 2020, **167**, 110520.
- 41 M. Wood, J. Li, R. E. Ruther, Z. Du, E. C. Self, H. M.



- Meyer, C. Daniel, I. Belharouak and D. L. Wood, *Energy Storage Materials*, 2020, **24**, 188–197.
- 42 N. V. Faenza, L. Bruce, Z. W. Lebens-Higgins, I. Plitz, N. Pereira, L. F. J. Piper and G. G. Amatucci, *Journal of The Electrochemical Society*, 2017, **164**, A3727.
- 43 R. Jung, R. Morasch, P. Karayaylali, K. Phillips, F. Maglia, C. Stinner, Y. Shao-Horn and H. A. Gasteiger, *Journal of The Electrochemical Society*, 2018, **165**, A132.
- 44 I. A. Shkrob, J. A. Gilbert, P. J. Phillips, R. Klie, R. T. Haasch, J. Bareño and D. P. Abraham, *Journal of The Electrochemical Society*, 2017, **164**, A1489–A1498.
- 45 X. Zhang, W. J. Jiang, X. P. Zhu, A. Mauger, Qilu and C. M. Julien, *Journal of Power Sources*, 2011, **196**, 5102–5108.
- 46 M. N. Al-Shroofy, *PhD thesis*, University of Kentucky, 2017.
- 47 L. C. Thomas.
- 48 S. J. Cho, C. C. Chung, S. Podowitz-Thomas and J. L. Jones, *Materials Chemistry and Physics*, 2019, **228**, 32–36.
- 49 N. Loeffler, J. Von Zamory, N. Laszczynski, I. Doberdo, G. T. Kim and S. Passerini, *Journal of Power Sources*, 2014, **248**, 915–922.
- 50 J. Liu, X. Lu and C. Wu, *Membranes*, 2013, **3**, 389–405.
- 51 B. G. Westphal and A. Kwade, *Journal of Energy Storage*, 2018, **18**, 509–517.
- 52 B. Westphal, H. Bockholt, T. Gunther, W. Haselrieder and A. Kwade, *ECS Transactions*, 2015, 57–68.
- 53 H. Zheng, L. Tan, G. Liu, X. Song and V. S. Battaglia, *Journal of Power Sources*, 2012, **208**, 52–57.
- 54 H. Bockholt, W. Haselrieder and A. Kwade, *Powder Technology*, 2016, **297**, 266–274.
- 55 J. Liu, B. Ludwig, Y. Liu, Z. Zheng, F. Wang, M. Tang, J. Wang, J. Wang, H. Pan and Y. Wang, *Advanced Materials Technologies*, 2017, 1700106.
- 56 W. B. Hawley, H. M. Meyer and J. Li, *Electrochimica Acta*, 2021, **380**, 138203.
- 57 N. Susarla, S. Ahmed and D. W. Dees, *Journal of Power Sources*, 2018, **378**, 660–670.
- 58 F. Font, B. Protas, G. Richardson and J. M. Foster, *Journal of Power Sources*, 2018, **393**, 177–185.
- 59 M. Malamataris, A. Charisi, S. Malamataris, K. Kachrimanis and I. Nikolakakis, *Processes 2020*, Vol. 8, Page 788, 2020, **8**, 788.
- 60 M. Baunach, S. Jaiser, S. Schmelzle, H. Nirschl, P. Scharfer and W. Schabel, *Drying Technology*, 2016, **34**, 462–473.
- 61 R. Vanholme, B. Demedts, K. Morreel, J. Ralph and W. Boerjan, *Plant Physiology*, 2010, **153**, 895–905.
- 62 J. Zhu, C. Yan, X. Zhang, C. Yang, M. Jiang and X. Zhang, *Progress in Energy and Combustion Science*, 2020, **76**, 100788.
- 63 J. Li, Z. Du, R. E. Ruther, S. J. An, L. A. David, K. Hays, M. Wood, N. D. Phillip, Y. Sheng, C. Mao, S. Kalnaus, C. Daniel and D. L. Wood, *Toward Low-Cost, High-Energy Density, and High-Power Density Lithium-Ion Batteries*, 2017.
- 64 M. Memm, A. Hoffmann and M. Wohlfahrt-Mehrens, *Electrochimica Acta*, 2018, **260**, 664–673.
- 65 Z. Du, C. J. Janke, J. Li, C. Daniel and D. L. Wood, *Journal of the Electrochemical Society*, 2016, **163**, A2776–A2780.
- 66 H. Zheng, G. Liu, X. Song, P. Ridgway, S. Xun and V. S. Battaglia, *Journal of The Electrochemical Society*, 2010, **157**, A1060.
- 67 *MTI Conductive Carbon Coated Aluminum Foil for Battery Cathode Substrate*, <https://www.mtixtl.com/ConductiveCarbonCoatedAluminumFoil>.
- 68 L. Qiao, U. Oteo, M. Martinez-Ibañez, A. Santiago, R. Cid, E. Sanchez-Diez, E. Lobato, L. Meabe, M. Armand and H. Zhang, *Nature Materials*, 2022, 455–462.
- 69 C. Pastor-Fernandez, W. Dhammika Widanage, J. Marco, M.-A. Gama-Valdez and G. H. Chouchelamane, 2016 IEEE Transportation Electrification Conference and Expo (ITEC), 2016, pp. 1–6.
- 70 H. Kang, C. Lim, T. Li, Y. Fu, B. Yan, N. Houston, V. De Andrade, F. De Carlo and L. Zhu, *Electrochimica Acta*, 2017, **232**, 431–438.
- 71 W. Haselrieder, S. Ivanov, D. K. Christen, H. Bockholt and A. Kwade, *ECS Transactions*, 2013, 50–59.
- 72 M. Li, J. Wei, L. Ren, Y. Zhao, Z. Shang, D. Zhou, W. Liu, L. Luo and X. Sun, *Cell Reports Physical Science*, 2021, **2**, 100374.
- 73 E. Billy, M. Joulié, R. Laucournet, A. Boulineau, E. De Vito and D. Meyer, *ACS Applied Materials and Interfaces*, 2018, **10**, 16424–16435.
- 74 L. Azhari, X. Zhou, B. Sousa, Z. Yang, G. Gao and Y. Wang, *ACS Applied Materials and Interfaces*, 2020, **12**, 57963–57974.
- 75 K. Sahni, M. Ashuri, Q. He, R. Sahore, I. D. Bloom, Y. Liu, J. A. Kaduk and L. L. Shaw, *Electrochimica Acta*, 2019, **301**, 8–22.
- 76 C. H. Jo, D. H. Cho, H. J. Noh, H. Yashiro, Y. K. Sun and S. T. Myung, *Nano Research*, 2015, **8**, 1464–1479.
- 77 H. Buqa, M. Holzapfel, F. Krumeich, C. Veit and P. Novák, *Journal of Power Sources*, 2006, **161**, 617–622.



- 78 C. C. Li and Y. W. Wang, *Journal of The Electrochemical Society*, 2011, **158**, A1361.
- 79 N. Loeffler, G. T. Kim, F. Mueller, T. Diemant, J. K. Kim, R. J. Behm and S. Passerini, *ChemSusChem*, 2016, **9**, 1112–1117.
- 80 N. V. Kosova, E. T. Devyatkina and V. V. Kaichev, *Journal of Power Sources*, 2007, **174**, 965–969.
- 81 K. Shizuka, C. Kiyohara, K. Shima and Y. Takeda, *Journal of Power Sources*, 2007, **166**, 233–238.
- 82 A. Kazzazi, D. Bresser, A. Birrozzi, J. von Zamory, M. Hekmatfar and S. Passerini, *ACS Applied Materials & Interfaces*, 2018, **10**, 17214–17222.
- 83 N. D. Phillip, C. Daniel and G. M. Veith, *Journal of The Electrochemical Society*, 2020, **167**, 040521.
- 84 L. Liang, X. Sun, C. Wu, L. Hou, J. Sun, X. Zhang and C. Yuan, *ACS Applied Materials and Interfaces*, 2018, **10**, 5498–5510.
- 85 Paulsen, *High nickel cathode material having low soluble base content*, 2012.
- 86 W. Bauer, F. A. Çetinel, M. Müller and U. Kaufmann, *Electrochimica Acta*, 2019, **317**, 112–119.
- 87 F. Lin, I. M. Markus, D. Nordlund, T.-C. Weng, M. D. Asta, H. L. Xin and M. M. Doeff, *Nature Communications 2014 5:1*, 2014, **5**, 1–9.
- 88 M. Jo, S. H. Park and H. Lee, *Materials (Basel, Switzerland)*, 2021, **14**, 4670.

