

PAPER • OPEN ACCESS

Recycled Wood Plastic Composites as Floor Panels for Ship Containers

To cite this article: Sotirios Grammatikos *et al* 2020 *IOP Conf. Ser.: Mater. Sci. Eng.* **842** 012006

View the [article online](#) for updates and enhancements.

Recent citations

- [M. Chandrasekar *et al*](#)
- [Low-cost emissions cuts in container shipping: Thinking inside the box](#)
Haris Doukas *et al*




The Electrochemical Society
Advancing solid state & electrochemical science & technology

The ECS is seeking candidates to serve as the
Founding Editor-in-Chief (EIC) of ECS Sensors Plus,
a journal in the process of being launched in 2021

The goal of ECS Sensors Plus, as a one-stop shop journal for sensors, is to advance the fundamental science and understanding of sensors and detection technologies for efficient monitoring and control of industrial processes and the environment, and improving quality of life and human health.

Nomination submission begins: May 18, 2021



Recycled Wood Plastic Composites as Floor Panels for Ship Containers

Sotirios Grammatikos^{1, a)}, Harald Bertin Jøsendal^{1, b)}, Styliani Papatzani^{2, 3, c)}, Orsa Boura^{1, d)}, Mohammad Hajmohammadian Baghban^{1, d)}

¹Group of Sustainable Composites, Department of Manufacturing and Civil Engineering, Norwegian University of Science and Technology, Gjøvik, Norway

²Hellenic Army Academy, Department of Mathematics and Engineering Sciences, Vari, Greece

³Hellenic Ministry of Culture, Directorate of Restoration of Medieval & Post-medieval Monuments, Athens, Greece

^a sotirios.grammatikos@ntnu.no

Abstract. Within the framework of this study, we aim at the replacement of plywood as ship containers floor material, with a lighter and friendlier-to-rainforests composite material. Wood fibre-reinforced thermoPlastic Composites (WPC) were developed using double-screw extrusion, consisting of recycled waste wood fibres reinforcing recycled High Density PolyEthylene (HDPE) matrix. This shift to WPCs has the dual positive effect of containers freight reduction as well as elimination of the use of natural resources, radically contributing to climate change measures. Following international shipping standards for container flooring, high quality recycled WPCs were developed. HDPE was found to provide acceptable structural performance. To that respect, WPC blends of HDPE matrix reinforced with 30%, 40% and 50%wt wood fibre flour, were fabricated and subjected to 3 point-bending mechanical testing. It was found that the studied WPCs reveal mechanical performance adequate to qualify as replacements of plywood timber flooring in ship containers.

1. Introduction

The increasing demand for greener transportation imposes the need for new environmental-friendly engineering materials to reduce carbon footprint and Green-House Emissions (GHE) [1, 2]. In total 72 million containers operate in off-shore and in-shore missions, a third of which is used for sea transportation [3]. Currently, all shipping containers come with a standard timber flooring based on plywood sourced from rainforests. Plywood's extensive use has led to the gradual disappearance of animal species as well as to the elimination of forests efficiency to capture CO₂ emissions [3].

At the same time, the majority of plastics and other polymer composites used in industries such as transportation and energy, end up in landfill or are being used for energy recovery mainly via incineration (according to The Incineration of Waste Directive, 2000/76/EC) [4]. A significant amount of wastes stemming from packaging or polymer composites ends up in landfill around Europe or other non-EU countries (EC Waste shipment regulations (259/93/EEC)) [5].

Together with plastics and other waste issues within the EU, around 700 Mt of bio-based waste mass is produced annually of which at present, only a small percentage is recovered or reused for economic benefit [6].



Therefore, it becomes apparent, that a holistic solution to preserve plywood and at the same time promote recycling is of primary importance. In this study, we aim at the development of Wood fibre-reinforced thermoPlastic Composites (WPC) as replacement of plywood as floor material of ship containers. WPC is a lighter and friendlier to the precious rainforests material replacement. This shift to WPCs as container floors has the dual positive effect of significantly reducing the freight of containers as well as eliminating the use of natural resources. This radically contributes to the environmental cost and paves the way towards circular economy. WPC were developed using double-screw extrusion, consisting of recycled waste wood fibres reinforcing recycled polyethylene (PE) [7, 8]. Following the tight international shipping standards for container flooring with respect to mechanical and hygrothermal performance, high quality lightweight recycled WCPs were developed. WPC blends of HDPE matrix reinforced with 30%, 40% and 50%wt wood fibre flour, were fabricated and subjected to 3 point-bending mechanical testing. It was found that the studied WPCs reveal acceptable mechanical properties and can qualify as candidate replacements of plywood timber flooring in ship containers.

2. Experimental procedure

2.1. Manufacturing

WPC were produced by a simple mixture of wood powder with thermoplastic polymers (figure 1). Before the mixing process, all raw materials were dried out in an oven at 60oC for 24hrs to remove moisture absorbed by the environment. Then, wood powder and the polymer matrix were mechanically mixed in their dry state (figure 2).



Figure 1. Raw materials employed for the production of WPC.



Figure 2. Raw materials employed for the production of WPC.

This mixture of figure 2 was then heated and placed within the extruder for extrusion into different profile shapes.

2.2. Mechanical testing

Three-point bending was employed to assess the mechanical performance of the developed WPC according to the ISO 178. Three-point bending was performed on a Zwick Z2.5 testing machine. All mechanical testing was conducted at room temperature conditions. Five standard specimens were fabricated and tested for each wood powder fraction (30%, 40% and 50%wt). Dogbone samples were prepared according to ISO A1 in dimensions of 50x28x305 mm.

3. Results and discussion

Figure 3 displays the flexural strength whereas figure 4 the flexural modulus of the fabricated WPCs, for the 3 different wood-powder volume fractions. As can be seen, flexural strength exhibits an increasing tendency with wood powder content increase from 30%wt to 50%wt. However, figure 4 demonstrates that flexural modulus increases significantly with the increase in wood powder content.

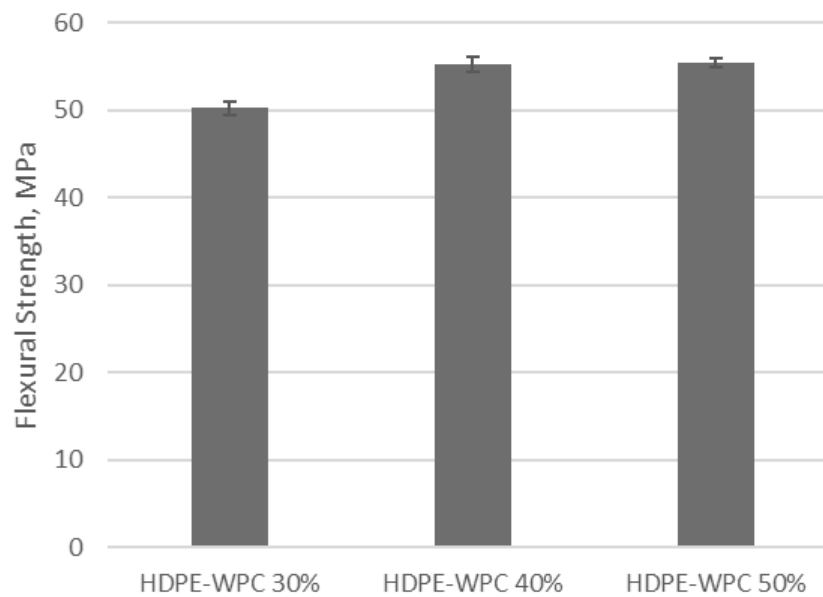


Figure 3. Flexural strength of the tested WPCs.

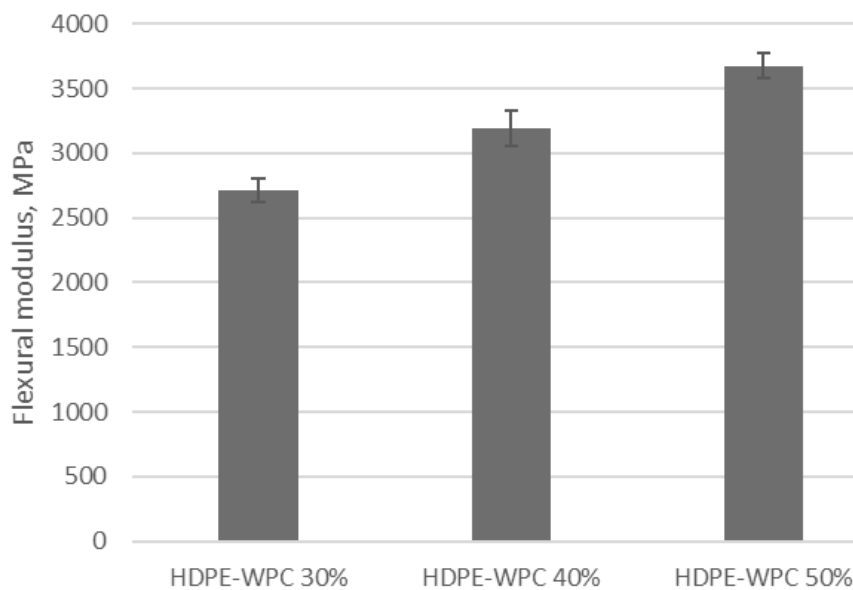


Figure 4. Flexural modulus of tested WPCs.

In order for the developed WPCs to qualify as a floor panel material for ship containers, they have to surpass the threshold of 65.9 MPa in flexural strength (according to the IICL TB 001 Performance standard for Structural Container Floor Panels) which is 10% higher than the WPC modified with 50%wt wood powder. This implies the fact that based on mechanical performance, the proposed WPCs are a promising sustainable material solution for the replacement of rainforest plywood in ship containers.

4. Conclusions

This study investigated the development of Wood Plastic Composites for potential replacement of plywood as ship containers floor material. WPCs were developed using double-screw extrusion, consisting of recycled waste wood fibres reinforcing recycled polyethylene (PE) matrix. WPC blends of HDPE matrix reinforced with 30%, 40% and 50%wt wood fibre flour, were fabricated and

subjected to 3 point-bending mechanical testing. It was found that the studied WPCs reveal mechanical performance adequate to qualify as replacements of plywood timber flooring in ship containers. This replacement contributes to containers freight reduction (less CO₂), minimization of the use of fossil fuels and recycling, radically contributing to climate change measures for future circular economy.

5. References

- [1] European Commission, Guidelines on financial incentives for clean and energy efficient vehicles, SWD, 27, 2013.
- [2] European Commission, Communication: Integrating maritime transport emissions in the EU's greenhouse gas reduction policies, COM 479, 2013.
- [3] Delpizzo, Rich, Haifeng Wang, and Andrew Panek. Sustainability in the Maritime Industry: A Collection of Relevant Papers. New York: Society of Naval Architects and Marine Engineers, Internet resource, 2011.
- [4] European Commission, Directive 2000/76/EC of the European Parliament and of the Council on the incineration of waste, 2008.
- [5] European Commission, Report from the Commission to the European Parliament and the Council on the implementation of regulation (EC) no 1013/2006 on shipments of waste, 2015.
- [6] N. Reynolds, M. Pharaoh, An introduction to composites recycling, in: V. Goodship (Ed.), Management Recycling and Reuse of Waste Composites, Woodhead Publishing, (2010) pp. 3–19.
- [7] M.C.S. Ribeiro, A.C. Meira-Castro, F.G. Silva, J. Santos, J.P. Meixedo, A. Fiúza, Reuse assessment of thermoset composite wastes as aggregate and filler replacement for concrete-polymer composite materials: a case study regarding GFRP pultrusion wastes, *Resour. Conserv. Recycl.*, 2015.
- [8] A. Yazdanbakhsh LC. Bank, C. Chen, Use of recycled FRP reinforcing bar in concrete as coarse aggregate and its impact on the mechanical properties of concrete, *Construction and Building Materials* 121, (2016) pp. 278–284.

Acknowledgments

This work was funded by the Regional Research Fund of Inland (Regionale Forskningsfond Innlandet - RFF Innlandet - Forprosjekt WPC [Project reference: 280223]), Oppland County, Norway. Authors would like to acknowledge Norner Research AS and Woodrock Group AS for the support.